



LJMU Research Online

Nasr, MS, Hussain, T, Kubba, H and Shubbar, AAF

Influence of Using High Volume Fraction of Silica Fume on Mechanical and Durability Properties of Cement Mortar

<http://researchonline.ljmu.ac.uk/id/eprint/13501/>

Article

Citation (please note it is advisable to refer to the publisher's version if you intend to cite from this work)

Nasr, MS, Hussain, T, Kubba, H and Shubbar, AAF (2020) Influence of Using High Volume Fraction of Silica Fume on Mechanical and Durability Properties of Cement Mortar. Journal of Engineering Science and Technology. 15 (4). pp. 2494-2506. ISSN 1823-4690

LJMU has developed [LJMU Research Online](#) for users to access the research output of the University more effectively. Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Users may download and/or print one copy of any article(s) in LJMU Research Online to facilitate their private study or for non-commercial research. You may not engage in further distribution of the material or use it for any profit-making activities or any commercial gain.

The version presented here may differ from the published version or from the version of the record. Please see the repository URL above for details on accessing the published version and note that access may require a subscription.

For more information please contact researchonline@ljmu.ac.uk

<http://researchonline.ljmu.ac.uk/>

INFLUENCE OF USING HIGH VOLUME FRACTION OF SILICA FUME ON MECHANICAL AND DURABILITY PROPERTIES OF CEMENT MORTAR

MOHAMMED SALAH NASR^{1,*}, THOLFELKAR HABEEB HUSSAIN²,
HUDA ZUHAIR KUBBA¹, ALI ABDULHUSSEIN SHUBBAR^{3, 4}

¹Babylon Technical Institute, Al-Furat Al-Awsat Technical University, 51015 Babylon, Iraq

²College of Water Resources Engineering, Al-Qasim Green University, Babylon, Iraq

³Department of Civil Engineering, Liverpool John Moores University, Henry Cotton
Building, Webster Street, Liverpool L3 2ET, UK

⁴ Department of Civil Engineering, College of Engineering,
University of Babylon, Babylon, Iraq

*Corresponding author: msn_alar@yaho.com, dw.moh1@atu.edu.iq

Abstract

The high pollution caused by CO₂ emission and the high level of energy consumed during cement manufacturing led the researchers to look for alternative techniques to reduce these environmental effects. One of these techniques includes reducing the content of cement in the mix by replacing it with supplementary cementitious materials such as fly ash, slag, silica fume, and so on. Many previous studies dealt with the utilizing of the high volume of supplementary cementitious materials, such as fly ash and slag. However, limited studies investigated the impact of silica fume on mortar or concrete properties in percentages of more than 30%. Thus, to produce environmentally friendly concrete, this study was performed to investigate the effect of the high replacement level of cement with silica fume on the properties of cement mortar. Six replacement proportions of silica fume (0%, 30%, 40%, 50%, 60% and 70%) were used in this paper. This paper used the flow rate, compressive strength, water absorption, bulk density and volume of permeable voids tests to test the effect of silica fume on different mortar characteristics. The results indicated that the best mixture among all other mixes was found by 50% substitution of silica fume. At this percentage, an enhancement in compressive strength of nearly 83%, 74% and 75% at 7, 28 and 56 days, respectively and an improvement in water absorption resistance by 8% compared to the control mixture were achieved.

Keywords: Bulk density, Compressive strength, High volume fraction, Silica fume.

1. Introduction

Concrete is the most used building material worldwide [1]. It can be used in various construction applications (such as dams, bridges, pavement and buildings). Cement is the major binder substance utilized in the manufacturing of concrete [2, 3]. It is anticipated that the fabrication of cement will be increased by approximately 400% relative to the production levels in 1990 as a result of the considerable expansion in the industry of construction [4].

Carbon emissions have been increased by nearly 30% in the atmosphere over the last century [5], which significantly changed the global climate [6-11] and consequently it caused serious environmental pollution and global warming [12-21]. The cement industry alone is in charge of about 5-8% of the CO₂ emissions worldwide [22-27]. Besides, the cement industry contributes to other air pollutants such as nitrogen oxide, sulphur dioxide, and carbon monoxide [28]. Furthermore, the cement industry generates about 30 million tons per year worldwide of a solid waste material called cement kiln dust [29]; and as it is known that the solid waste treatment requires proper landfills and complicated management plans [30-32]. Therefore, the cement industry has a significant impact on climate change and sustainable development [33, 34]. Additionally, cement manufacture is deemed one of the industries that require intensive energy and associated with the consuming of natural resources. In order to reduce these effects, supplementary cementitious materials (for example silica fume, limestone, fly ash, rice husk ash, and so on) are used as an alternative to cement [35, 36]. Additionally, the sludge of water and wastewater treatment plants, especially from electrocoagulation plants, was recycled in concrete [37-51]. The utilization of such substances in the manufacturing of cement has twofold profits by decreasing the negative environmental impact of cement and can reduce the volume of solid waste [52].

Silica fume (SF) is a by-product material produced during the manufacture of silicon metal in the electrical furnace [53]. SF is a non-crystalline (amorphous) silica. It has a high pozzolanic reaction when used in cement and concrete [53]. Many surveys have been made previously to study the impact of SF on various characteristics of concrete and mortar [54]. Bhanja and Sengupta [55] investigated the effect of SF (within the range of 0% to 25%) on the mechanical performance of concrete with water/binder ratios within the range between 0.26 to 0.42. Compressive and splitting tensile strength tests were executed in that study. It was demonstrated that the concrete compressive strength and tensile strength improved with increasing the SF content. Furthermore, in the same study, it was reported that the optimum replacement proportion of SF was depended on the water/ binder ratio of the mix. Mohamed [56] studied the effect of different percentages of fly ash and/or SF as cement replacement materials on the compressive strength of self-compacting concrete. It was revealed that replacing the cement with 15% SF gave higher strength than those with fly ash and without replacement mixes. A comparison between the effect of SF, fly ash and metakaolin on the mechanical and durability properties of mortar was performed by Mardani-Aghabaglou et al. [57]. It was stated that replacing the cement with 10% SF indicated higher compressive strength and lower water absorption than all other mixes. Çakır and Sofyanlı [58] investigated the influence of SF on the performance of recycled aggregate concrete (RAC). It was concluded that using 10% proportion of SF as cement replacement enhanced the mechanical and physical characteristics and significantly decrease the volumetric water absorption of RAC in comparison with plain RAC.

SF was used in the literature as a cement replacement material within the range (5-30%) [59-61]. Limited studies were conducted with higher replacement ratios (more than 30%). This is owing to the high initial cost of SF as compared with ordinary Portland cement (OPC). However, it was reported previously [62] that though the cost of SF concrete was more than OPC concrete, the environmental assessment indicated that the CO₂ emission was reduced significantly after replacing cement with SF. Additionally, it was stated in the same work [62] that the extended service life and long term benefits might overcome the high initial cost of SF. Therefore, in order to produce environmentally and clean concrete as well as to add some data to the open literature about the impact of high volume fraction of SF on mortar properties, this experimental study is performed. It aims to examine the consequence of the high replacement level of cement with SF (30%-70%) on some mechanical and durability properties of cement mortar. The investigated properties were the flow rate, compressive strength, bulk density, water absorption, and volume of permeable voids.

2. Materials and methodology

2.1. Materials

2.1.1. Binder materials

The materials utilized in the production of mortar were cement and SF. The cement used in this investigation was lime cement (Type CEM II/A-L 42.5R). The fineness and chemical composition of cement (Table 1) conform to the Iraqi standards NO.5 [63]. The initial and final setting times of the cement are shown in Table 2. The SF was purchased from BASF (Baden Aniline and Soda Factory) company. The fineness and chemical properties of SF (which is conformed to ASTM C1240 [64]) are illustrated in Table 1. The properties of SF are adopted from Mozan and Khalil [65]. Where the same materials were used in this study.

Table 1. The fineness and chemical composition of cement and SF.

Oxide	Cement	SF
CaO %	62.1	0.65
SiO ₂ %	22.1	90.2
Al ₂ O ₃ %	4.2	0.24
Fe ₂ O ₃ %	3.9	2.4
MgO %	3.3	0.41
SO ₃ %	1.9	0.4
L.O.I.	3.1	3.33
Blaine Fineness (m ² /kg)	3600	21000

Table 2. The physical specification of cement.

Property	Value
Initial setting time (min)	105
Final setting time (min)	150

The fineness of the binder materials has a considerable effect on the mechanical performance of the mortar and concrete. Shubbar et al. [66] stated that the compressive strength obtained is increased with the increasing of the fineness of the binder materials. As observed from Table 1 that the SF has higher fineness than

the cement, thus it is expected that the presence of the SF would improve the performance of the mortar during the hydration reaction.

2.1.2. Sand

Natural sand was used that graduated to comply with the Iraqi standard NO.45 [67] requirements, the grading of the natural sand is shown in Table 3.

Table 3. The grading of the natural sand.

Sieve opening, mm	Accumulative passing, %
10	100
4.75	100
2.36	100
1.18	75
0.60	36
0.3	23.5
0.15	2.5

2.1.3. Superplasticizer

Superplasticizer called Glenium 54 conforms to ASTM C494 Type A and F [68] was used as a workability adjuster.

2.1.4. Water

Tap water (City of Babylon) was used during this investigation.

2.2. Methodology

The mix proportions for all mixes were 1:2.75 (cement + SF: sand) and the water/binder ratio was fixed as 0.485. Six replacement proportions of SF by weight of cement were used: 0%, 30%, 40%, 50%, 60% and 70%. The mixes details are presented in Table 4.

Table 4. Mix proportion details of the mortar prepared with different proportions of Cement and SF.

Mix symbol	Cement (g)	SF (g)	SF (%)	Sand (g)	Water (g)	Superplasticizer, % of cement
0SF	500	0	0	1375	242	0
30SF	350	150	30	1375	242	0.75
40SF	300	200	40	1375	242	1.05
50SF	250	250	50	1375	242	1.5
60SF	200	300	60	1375	242	2.1
70SF	150	350	70	1375	242	2.5

The procedures provided by ASTM C109 [69] for mixing and compaction were followed for all mixes. The SF was added together with cement and sand, while the superplasticizer was mixed with the mixing water before adding. The flow rate of fresh mortar was measured immediately after mixing as described in ASTM C1437 [70]. The compressive strength, water absorption, bulk density and volume of permeable voids tests were performed for the hardened mortars. The detailed procedures of ASTM C642

[71] were taken into account for measuring the water absorption, bulk density, and volume of permeable voids using Eqs. (1), (2) and (3), respectively:

$$A = \frac{B-C}{B} \times 100 \quad (1)$$

$$G = \frac{C}{D-F} \times 1000 \quad (2)$$

$$V = \frac{D-C}{D-F} \times 100 \quad (3)$$

where,

A : water absorption after immersion (%).

B : the mass of the wet specimen in the air after immersion (g).

C : the mass of the oven-dry specimen in the air (g).

G : dry bulk density (Mg/m³).

D : the mass of the wet specimen in the air after boiling and immersion (g).

F : the mass of the wet specimen in water after boiling and immersion (g).

Standard 50 mm cubes were utilized for the mortar compressive strength, water absorption and bulk density tests. Three test ages were considered for the compressive strength (7, 28 and 56 days) and one age (56 days) for the other tests. A number of 72 cubes (54 cubes for compressive strength test and 18 cubes for water absorption, bulk density and volume of permeable voids tests) were made for this study.

3. Results and Discussions

3.1. Flow rate

Results of flow rates of fresh mortars are presented in Fig.1.

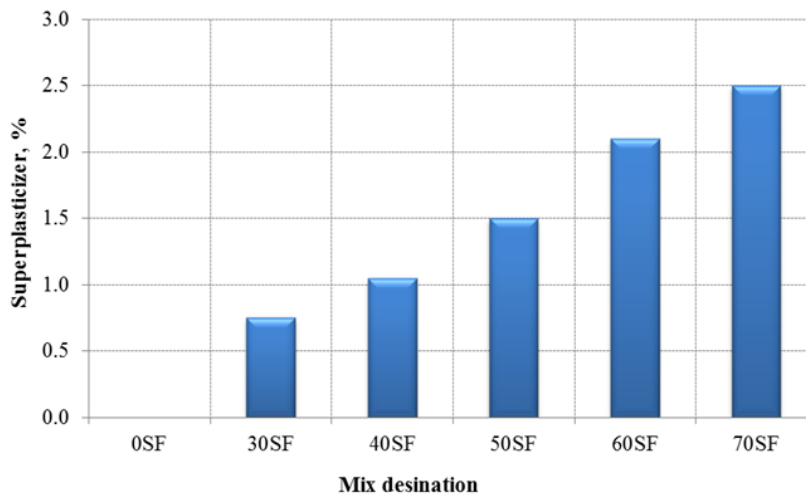


Fig. 1. Variation of Superplasticizer dosage with the content of silica fume in the Mix.

The SP dosage was varied from 0 to 2.5% of cement weight to maintain the flow rate values within the range of 200 ± 20 mm. It can be shown from the figure that, for the flow to be within the specified range, the SP dosage was increased with the increase of SF content in the mix. This increase in SP demand is owing to the absorption of SP by SF particles as a result of the high surface area of SF which leads to reducing the available amount of SP in the solution [60].

3.2. Compressive strength

The results of the compressive strength of the mortars after 7, 28 and 56 days of water curing at ambient temperature are presented in Fig. 2.

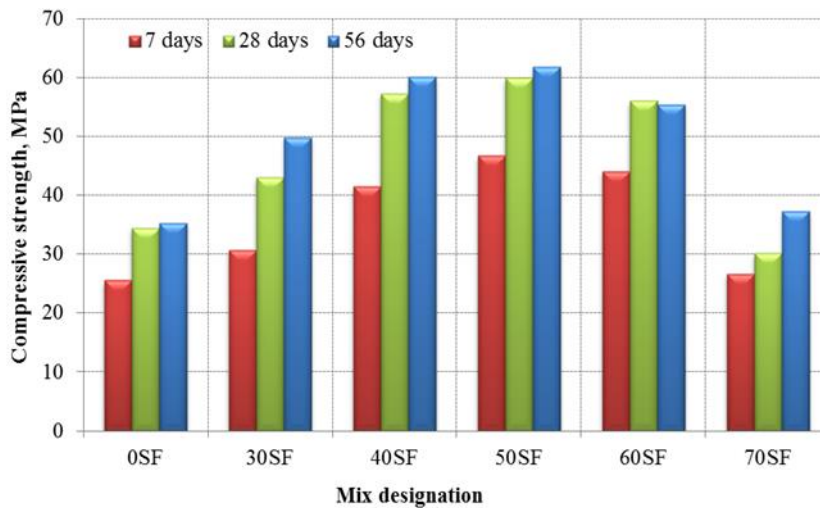


Fig. 2. Compressive strength results of mortar prepared with different proportions of cement and SF after 7, 28 and 56 days of curing.

In general, in a comparison with the control mixture (0% SF), it can be observed that substitution the cement with up to 70% SF enhanced the compressive strength property for all considered ages, except 70% replacement at 28 days which reduces the strength by about 13%. This enhancement in the compressive strength could be a result of the strengthening of the aggregate-paste bond [72] and chemical reaction between SF and calcium hydroxide which produces an additional C-S-H gel that thickens the microstructure and leads finally to strength enhancement [73]. At all curing ages, the maximum enhancement was recorded for mixtures with 50% SF. The improvements related to the control mix were 83%, 74% and 75% at 7, 28, and 56 days, respectively. Although it decreased the compressive strength at the age of 28 days, the mixture with 70% proportion of SF awarded minimum strength increasing than other SF mixtures at 7 and 56 days (about 4%, and 6%, respectively) compared to control mixture.

It can be seen also from Fig. 2 that the development of strength for replacement range of 30%-50% continue approximately in a similar manner at early and later ages. Other meaning, the low content of cement did not have a high effect on the rate of the pozzolanic reaction of the SF. However, beyond 50% substitution of SF (for the 60%-70% replacement levels), the compressive strength of mortar mixtures

for all considered ages (7, 28 and 56 days) tended to decrease from its highest value. This behaviour could be attributed to the low content of calcium hydroxide (which represents the main component that reacts with SF in the pozzolanic reaction) in the matrix as a result of the decreasing of cement content that leads finally a part of SF to act as a filler [74].

3.3. Water absorption

The water absorption results of mortars incorporated different proportions of SF as a replacement to cement after 56 days are presented in Fig. 3.

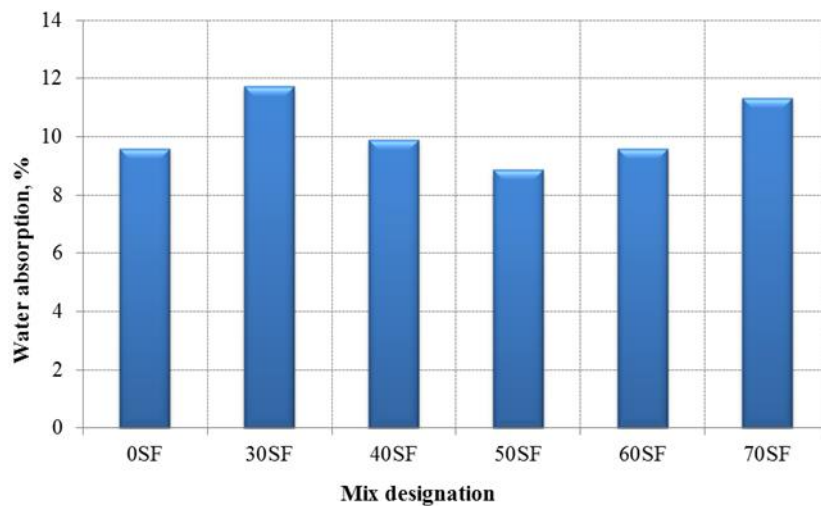


Fig. 3. Water absorption results of mortar prepared with different proportions of cement and SF after 56 days of curing.

Water absorption is considered as one of the main mechanisms (in addition to the diffusion and permeability) by which the transporting of the aggressive agents into the concrete is affected [75]. So, producing concrete with low water absorption is necessary to increase the service life of the concrete. As cleared from Fig. 3 that the mixtures with 30%, 40% and 70% SF have shown higher water absorption rate than that of the control mixture with about 22%, 3% and 18%, respectively. The results also indicated that the mixture with 60% SF has almost the same water absorption relative to the control mixtures. Additionally, Fig. 3 reveals that the mixture with 50% SF reduced the water absorption rate by about 8% relative to the control mixture. These findings were harmonious with the enhancement in the compressive strength gained for the mixture with 50% SF.

3.4. Bulk density

Figure 4 presents the bulk density results for mortars prepared with different proportions of SF as a replacement to cement after 56 days.

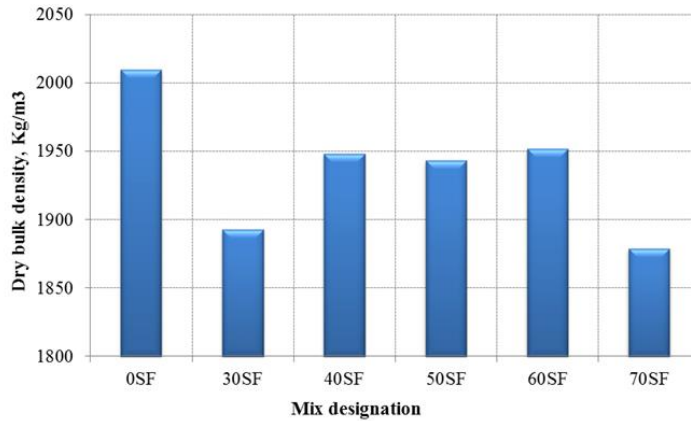


Fig. 4. Dry bulk density of mortar prepared with different proportions of cement and SF after 56 days of curing.

It was found that the replacing of cement with different percentages of SF reduces the bulk density of mortar mixes with disproportionate rates. The lowest density of about 6.5% relative to the control mixture was given by 70% replacement. However, replacing the cement by 30%, 40%, 50% and 60% of with SF caused a reduction in the dry bulk density by about 5.8%, 3%, 3.3% and 2.9%, respectively, in comparison to the control mix. The varying in the density of hardened concrete or mortar are govern by the cement and water contents, the density of aggregate, and the entrapped air or entrained air voids [75]. Therefore, accordingly, replacing the cement with a material with lower specific gravity than cement such as SF can reduce the density of the hardened mortar.

3.5. Volume of permeable voids

The results of permeable pore space (voids) volume for the mortar incorporated different proportions of SF are given in Fig. 5.

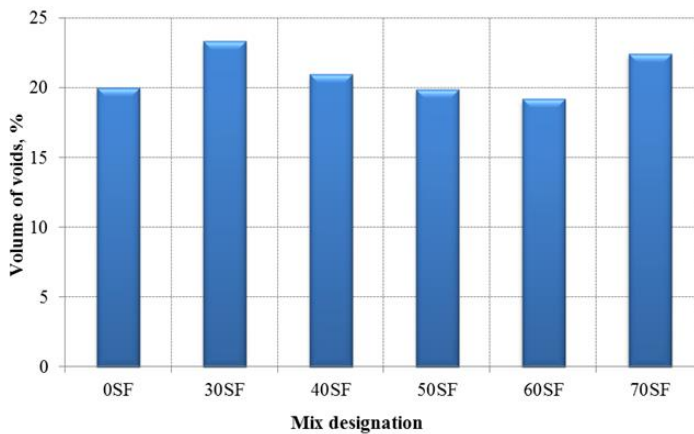


Fig. 5. Volume percent of permeable voids of mortar prepared with different proportions of cement and SF after 56 days of curing.

Results indicated that the higher the SF in the mix up to 60%, the lower the volume of permeable voids. This behaviour is attributed to the filling influence and the pozzolanic reaction of the SF [76]. However, there was no significant decreasing in the volume of permeable voids in comparison with the control mix, where, only 4% was the decreasing rate of the voids volume at 60% replacement of SF, which was the maximum improvement. On the other hand, replacing the cement with 70 % SF led to increase the voids volume by 12% related to the control specimen.

4. Conclusions

This study was conducted with the aim of investigating the impact of using a high volume fraction of SF on some properties of cement mortar. Based on the results of the present study, the following conclusions are noticed:

- The SF increases the superplasticizer demand in the fresh mortar. The higher the SF content in the mix, the higher the SP amount required to maintain the specified flow rate.
- High replacement level of cement with SF up to 50% can significantly enhance the compressive strength of mortar at earlier (7 days) and later ages (28 and 56 days). The optimum enhancement was achieved for the mixture with 50% SF. Where, the increasing rates of compressive strength are 83%, 74% and 75% at 7, 28, and 56 days, respectively in comparison to the control sample.
- Using higher proportions of SF up to 70% increases the water absorption rate of the cement mortar, except the mixture with 50% SF that indicated a lower water absorption rate by about 8% relative to the control mix.
- Replacing the cement with 70% of SF decreased the bulk density of cement mortar by 6.5% related to those mixtures without SF.
- There is no significant enhancement in the volume of permeable pores percent after incorporating a high amount of SF in mortar mixes. The farthest amendment is realized at 60% SF replacement (about 4%) in comparison to the reference sample.
- It can be concluded from this experimental investigation that it is possible to manufacture a green mortar in which the cement can be replaced with 50% SF with a significant improvement in the mechanical properties and water absorption resistance.

Abbreviations

BASF	Baden Aniline and Soda Factory
OPC	Ordinary Portland cement
RAC	Recycled aggregate concrete
SF	Silica fume
SP	Superplasticizer

References

1. Nasr, M.S.; Hussain, T.H.; and Najim, W.N. (2018). Properties of cement mortar containing biomass bottom ash and sanitary ceramic wastes as a partial replacement of cement. *International Journal of Civil Engineering and Technology*, 9(10), 153-165.

2. Li, X.; Korayem, A.H.; Li, C.; Liu, Y.; He, H.; Sanjayan, J.G.; and Duan, W.H. (2016). Incorporation of graphene oxide and silica fume into cement paste: A study of dispersion and compressive strength. *Construction and Building Materials*, 123, 327-335.
3. Hasan, Z.A.; Nasr, M.S.; and Abed, M.K. (2019). Combined effect of silica fume, and glass and ceramic waste on properties of high strength mortar reinforced with hybrid fibers. *International Review of Civil Engineering* 10(5), 327-335.
4. Damtoft, J.S.; Lukasik, J.; Herfort, D.; Sorrentino, D.; and Gartner, E.M. (2008). Sustainable development and climate change initiatives. *Cement and Concrete Research*, 38(2), 115-127.
5. Millar, R.; Allen, M.; Rogelj, J.; and Friedlingstein, P. (2016). The cumulative carbon budget and its implications. *Oxford Review of Economic Policy*, 32(2), 323-342.
6. Ryecroft, S.; Shaw, A.; Fergus, P.; Kot, P.; Hashim, K.; Moody, A.; and Conway, L. (2019). A first implementation of underwater communications in raw water using the 433 MHz frequency combined with a bowtie antenna. *Sensors*, 19(8), 1813-1823.
7. Ryecroft, S.P.; Shaw, A.; Fergus, P.; Kot, P.; Hashim, K.; and Conway, L. (2020). A novel gesomin detection method based on microwave spectroscopy. *Proceedings of the 12th International Conference on Developments in eSystems Engineering (DeSE)*. Kazan, Russia, 14-23.
8. Al-Jumeily, D.; Hashim, K.; Alkaddar, R.; Al-Tufaily, M.; and Lunn, J. (2019). Sustainable and environmental friendly ancient reed houses (Inspired by the past to motivate the future). *Proceedings of the 11th International Conference on Developments in eSystems Engineering (DeSE)*. Cambridge, UK, 214-219.
9. Zubaidi, S.L.; Al-Bugharbee, H.; Muhsen, Y.R.; Hashim, K.; Alkhaddar, R.M.; Al-Jumeily, D.; and Aljaaf, A.J. (2019). The prediction of municipal water demand in Iraq: a case study of Baghdad governorate. *Proceedings of the 12th International Conference on Developments in eSystems Engineering (DeSE)*. Kazan, Russia, 274-277.
10. Zubaidi, S.L.; Ortega-Martorell, S.; Kot, P.; Alkhaddar, R.M.; Abdellatif, M.; Gharghan, S.K.; Ahmed, M.S.; and Hashim, K. (2020). A method for predicting long-term municipal water demands under climate change. *Water Resources Management*, 34(3), 1265-1279.
11. Majdi, H.S.; Shubbar, A.; Nasr, M.S.; Al-Khafaji, Z.S.; Jafer, H.; Abdulredha, M.; Masoodi, Z.A.; Sadique, M.; and Hashim, K. (2020). Experimental data on compressive strength and ultrasonic pulse velocity properties of sustainable mortar made with high content of GGBFS and CKD combinations. *Data in Brief*, 13, 105961-105972.
12. Abdulhadi, B.A.; Kot, P.; Hashim, K.S.; Shaw, A.; and Khaddar, R.A. (2019). Influence of current density and electrodes spacing on reactive red 120 dye removal from dyed water using electrocoagulation/electroflotation (EC/EF) process. *Proceedings of the First International Conference on Civil and Environmental Engineering Technologies (ICCEET)*. University of Kufa, Iraq, 12-22.
13. Al-Saati, N.H.; Hussein, T.K.; Abbas, M.H.; Hashim, K.; Al-Saati, Z.N.; Kot, P.; Sadique, M.; Aljefery, M.H.; and Carnacina, I. (2019). Statistical modelling

- of turbidity removal applied to non-toxic natural coagulants in water treatment: a case study. *Desalination and Water Treatment*, 150, 406-412.
14. Emamjomeh, M.M.; Mousazadeh, M.; Mokhtari, N.; Jamali, H.A.; Makkiabadi, M.; Naghdali, Z.; Hashim, K.S.; and Ghanbari, R. (2019). Simultaneous removal of phenol and linear alkylbenzene sulfonate from automotive service station wastewater: Optimization of coupled electrochemical and physical processes. *Separation Science and Technology*, 1, 1-11.
 15. Hashim, K.; Kot, P.; Zubaid, S.; Alwash, R.; Al Khaddar, R.; Shaw, A.; Al-Jumeily, D.; and Aljefery, M. (2020). Energy efficient electrocoagulation using baffle-plates electrodes for efficient *Escherichia Coli* removal from Wastewater. *Journal of Water Process Engineering*, 33(20), 101079-101086.
 16. Hashim, K.S. (2017). *The innovative use of electrocoagulation-microwave techniques for the removal of pollutants from water*. Ph.D. Thesis. Civil Engineering Liverpool John Moores University, Liverpool, United Kingdom.
 17. Hashim, K.S.; Al-Saati, N.H.; Alquzweeni, S.S.; Zubaidi, S.L.; Kot, P.; Kraidi, L.; Hussein, A.H.; Alkhaddar, R.; Shaw, A.; and Alwash, R. (2019). Decolourization of dye solutions by electrocoagulation: an investigation of the effect of operational parameters. *Proceedings of the First International Conference on Civil and Environmental Engineering Technologies (ICCEET)*. University of Kufa, Iraq, 25-32.
 18. Zubaidi, S.L.; Kot, P.; Hashim, K.; Alkhaddar, R.; Abdellatif, M.; and Muhsin, Y.R. (2019). Using LARS –WG model for prediction of temperature in Columbia city, USA. *Proceedings of the First International Conference on Civil and Environmental Engineering Technologies (ICCEET)*. University of Kufa, Iraq, 31-38.
 19. Hashim, K.S.; Alkhaddar, R.; Shaw, A.; Kot, P.; Al-Jumeily, D.; Alwash, R.; and Aljefery, M.H. (2020). *Electrocoagulation as an eco-friendly River water treatment method; in Advances in Water Resources Engineering and Management* (1st ed.). Berlin: Springer.
 20. Zubaidi, S.; Al-Bugharbee, H.; Ortega Martorell, S.; Gharghan, S.; Olier, I.; Hashim, K.; Al-Bdairi, N.; and Kot, P. (2020). A novel methodology for prediction urban water demand by wavelet denoising and adaptive neuro-fuzzy inference system approach. *Water*, 12(6), 1-17.
 21. Zubaidi, S.L.; Ortega-Martorell, S.; Al-Bugharbee, H.; Olier, I.; Hashim, K.S.; Gharghan, S.K.; Kot, P.; and Al-Khaddar, R. (2020). Urban water demand prediction for a city that suffers from climate change and population growth: gauteng province case study. *Water*, 12(7), 1-18.
 22. Nasr, M.S.; Hasan, Z.A.; and Abed, M.K. (2019). Mechanical properties of cement mortar made with black tea waste ash as a partial replacement of cement. *Engineering and Technology Journal*, 37(1), 45-48.
 23. Shubbar, A.A.; Al-Shaer, A.; Alkizwini, R.S.; Hashim, K.; Al Hawesah, H.; and Sadique, M. (2019). Investigating the influence of cement replacement by high volume of GGBS and PFA on the mechanical performance of cement mortar. *IOP Conference Series: Materials Science and Engineering*, 584(1), 1-7.
 24. Shubbar, A.; Jafer, H.M.; Dulaimi, A.; Atherton, W.; and Al-Rifaie, A. (2017). The development of a low carbon cementitious material produced from cement, ground granulated blast furnace slag and high calcium fly ash.

International Journal of Civil, Environmental, Structural, Construction and Architectural Engineering, 11(7), 905-908.

25. Shubbar, A.A.; Sadique, M.; Shanbara, H.K.; and Hashim, K. (2020). The development of a new low carbon binder for construction as an alternative to cement, in advances in sustainable construction. *Materials and Geotechnical Engineering* (1st ed.). Berlin: Springer.
26. Shubbar, A.A.; Sadique, M.; Kot, P.; and Atherton, W. (2019). Future of clay-based construction materials—A review. *Construction and Building Materials*, 210, 172-187.
27. Kubba, H.Z.; Nasr, M.S.; Al-Abdaly, N.M.; Dhahir, M.K.; and Najim, W.N. (2020). Influence of incinerated and non-incinerated waste paper on properties of cement mortar. *IOP Conferences Series: Materials Science and Engineering*, 67(3), 1-11.
28. Lei, Y.; Zhang, Q.; Nielsen, C.; and He, K. (2011). An inventory of primary air pollutants and CO₂ emissions from cement production in China, 1990–2020. *Atmospheric Environment*, 45(1), 147-154.
29. Singh, T.; Patnaik, A.; and Chauhan, R. (2016). Optimization of tribological properties of cement kiln dust-filled brake pad using grey relation analysis. *Materials & Design*, 89, 1335-1342.
30. Idowu, I.A.; Atherton, W.; Hashim, K.; Kot, P.; Alkhaddar, R.; Alo, B.I.; and Shaw, A. (2019). An analyses of the status of landfill classification systems in developing countries: Sub Saharan Africa landfill experiences. *Waste Management*, 87, 761-771.
31. Abdulredha, M.; Al Khaddar, R.; Jordan, D.; Kot, P.; Abdulridha, A.; and Hashim, K. (2018). Estimating solid waste generation by hospitality industry during major festivals: A quantification model based on multiple regression. *Waste Management*, 77, 388-400
32. Markewitz, P.; Zhao, L.; Ryssel, M.; Moumin, G.; Wang, Y.; Sattler, C.; Robinius, M.; and Stolten, D. (2019). Carbon capture for CO₂ emission reduction in the cement industry in Germany. *Energies*, 12(12), 2432-2443.
33. Markewitz, P.; Zhao, L.; Ryssel, M.; Moumin, G.; Wang, Y.; Sattler, C.; Robinius, M.; and Stolten, D. (2019). Carbon capture for CO₂ emission reduction in the cement industry in Germany. *Energies*, 12(12), 2432-2443.
34. Malhotra, V. (2010). Global warming, and role of supplementary cementing materials and superplasticisers in reducing greenhouse gas emissions from the manufacturing of portland cement. *International Journal of Structural Engineering*, 1(2), 116-130.
35. Hussain, T.H.; Nasr, M.S.; and Salman, H.J. (2019). Effect of elevated temperature on degradation behaviour of reactive powder concrete made with rubber tire wastes as an aggregate replacement. *ARPJ Journal of Engineering and Applied Sciences*, 14(3), 775–780.
36. Nayel, I.; Burhan, S.; and Nasr, M. (2018). Characterisation of prepared rice husk ash and its effects on strength development in recycled aggregate concrete. *OP Conference Series: Materials Science and Engineering*, 671(1), 1-12.

37. Sharma, P.; and Joshi, H. (2016). Utilization of electrocoagulation-treated spent wash sludge in making building blocks. *International Journal of Environmental Science and Technology*, 13(1), 349-358.
38. Alattabi, A.W.; Harris, C.; Alkhaddar, R.; Alzeyadi, A.; and Hashim, K. (2017). Treatment of residential complexes' wastewater using environmentally friendly technology. *Procedia Engineering*, 196, 792-799.
39. Alattabi, A.W.; Harris, C.B.; Alkhaddar, R.M.; Hashim, K.S.; Ortoneda-Pedrola, M.; and Phipps, D. (2017). Improving sludge settleability by introducing an innovative, two-stage settling sequencing batch reactor. *Journal of Water Process Engineering*, 20, 207-216.
40. Hashim, K.S.; Idowu, I.A.; Jasim, N.; Al Khaddar, R.; Shaw, A.; Phipps, D.; Kot, P.; Pedrola, M.O.; Alattabi, A.W.; and Abdulredha, M. (2018). Removal of phosphate from River water using a new baffle plates electrochemical reactor. *MethodsX*, 5, 1413-1418.
41. Hashim, K.S.; Khaddar, R.A.; Jasim, N.; Shaw, A.; Phipps, D.; Kota, P.; Pedrola, M.O.; Alattabi, A.W.; Abdulredha, M.; and Alawsh, R. (2018). Electrocoagulation as a green technology for phosphate removal from River water. *Separation and Purification Technology*, 210, 135-144.
42. Hashim, K.S.; Shaw, A.; Al Khaddar, R.; Ortoneda Pedrola, M.; and Phipps, D. (2017). Defluoridation of drinking water using a new flow column-electrocoagulation reactor (FCER) - Experimental, statistical, and economic approach. *Journal of Environmental Management*, 197, 80-88.
43. Hashim, K.S.; Shaw, A.; Al Khaddar, R.; Pedrola, M.O.; and Phipps, D. (2017). Iron removal, energy consumption and operating cost of electrocoagulation of drinking water using a new flow column reactor. *Journal of Environmental Management*, 189, 98-108.
44. Hashim, K.S.; Shaw, A.; Al Khaddar, R.; Pedrola, M.O.; and Phipps, D. (2017). Energy efficient electrocoagulation using a new flow column reactor to remove nitrate from drinking water - Experimental, statistical, and economic approach. *Journal of Environmental Management*, 196, 224-233.
45. Hashim, K.S.; Ali, S.M.; Alrifaie, J.K.; Kot, P.; Shaw, A.; Khaddar, R.A.; Idowu, I.; and Gkantou, M. (2020). Escherichia coli inactivation using a hybrid ultrasonic-electrocoagulation reactor. *Chemosphere*, 247, 125868-125875.
46. Hashim, K. S.; Alkhaddar, R.; Shaw, A.; Kot, P.; Al-Jumeily, D.; Alwash, R.; and Aljefery, M. H. (2020). *Electrocoagulation as an eco-friendly River water treatment method*, in *Advances in Water Resources Engineering and Management* (1st ed.). Berlin: Springer.
47. Hashim, K.S.; Al-Saati, N.H.; Hussein, A.H.; and Al-Saati, Z.N. (2018). An investigation into the level of heavy metals leaching from canal-dredged sediment: a case study metals leaching from dredged sediment. *Proceedings of the First International Conference on Materials Engineering & Science*. Istanbul Aydin University (IAU), Turkey, 12-22.
48. Hashim, K.S.; Hussein, A.H.; Zubaidi, S.L.; Kot, P.; Kraidi, L.; Alkhaddar, R.; Shaw, A.; and Alwash, R. (2019). Effect of initial pH value on the removal of reactive black dye from water by electrocoagulation (EC) method. *Proceedings of the 2nd International Scientific Conference*. Al-Qadisiyah University, Iraq 12-22.

49. Omran, I.I.; Al-Saati, N.H.; Hashim, K.S.; Al-Saati, Z.N.; P., K.; Khaddar, R. A.; Al-Jumeily, D.; Shaw, A.; Ruddock, F.; and Aljefery, M. (2019). Assessment of heavy metal pollution in the Great Al-Mussaib irrigation channel. *Desalination and Water Treatment*, 168, 165-174.
50. Gkantou, M.; Muradov, M.; Kamaris, G.S.; Hashim, K.; Atherton, W.; and Kot, P. (2019). Novel electromagnetic sensors embedded in reinforced concrete beams for crack detection. *Sensors*, 19(23), 5175-5189.
51. Teng, K.H.; Kot, P.; Muradov, M.; Shaw, A.; Hashim, K.; Gkantou, M.; and Al-Shamma'a, A. (2019). Embedded smart antenna for non-destructive testing and evaluation (NDT&E) of moisture content and deterioration in concrete. *Sensors*, 19(3), 547-559.
52. Chandra Paul, S.; Mbewe, P.B.; Kong, S.Y.; and Šavija, B. (2019). Agricultural solid waste as source of supplementary cementitious materials in developing countries. *Materials*, 12(7), 1112.
53. Amin, M.; and Hashem, F. (2011). Hydration characteristics of hydrothermal treated cement kiln dust–sludge–silica fume pastes. *Construction and Building Materials*, 25(4), 1870-1876.
54. Abed, M.; Nasr, M.; and Hasan, Z. (2018). Effect of silica fume/binder ratio on compressive strength development of reactive powder concrete under two curing systems. *Proceedings of the 3rd International Conference on Buildings, Construction and Environmental Engineering*, 2(1), 1-8.
55. Bhanja, S.; and Sengupta, B. (2005). Influence of silica fume on the tensile strength of concrete. *Cement and Concrete Research*, 35(4), 743-747.
56. Mohamed, H.A. (2011). Effect of fly ash and silica fume on compressive strength of self-compacting concrete under different curing conditions. *Ain Shams Engineering Journal*, 2(2), 79-86.
57. Mardani-Aghabaglou, A.; Sezer, G.İ.; and Ramyar, K. (2014). Comparison of fly ash, silica fume and metakaolin from mechanical properties and durability performance of mortar mixtures view point. *Construction and Building Materials*, 70, 17-25.
58. Çakır, Ö.; and Sofyanlı, Ö.Ö. (2015). Influence of silica fume on mechanical and physical properties of recycled aggregate concrete. *HBRC Journal*, 11(2), 157-166.
59. Nili, M.; and Ehsani, A. (2015). Investigating the effect of the cement paste and transition zone on strength development of concrete containing nanosilica and silica fume. *Materials & Design*, 75, 174-183.
60. Sabet, F.A.; Libre, N.A.; and Shekarchi, M. (2013). Mechanical and durability properties of self consolidating high performance concrete incorporating natural zeolite, silica fume and fly ash. *Construction and Building Materials*, 44, 175-184.
61. Benaicha, M.; Roguiez, X.; Jalbaud, O.; Burtschell, Y.; and Alaoui, A.H. (2015). Influence of silica fume and viscosity modifying agent on the mechanical and rheological behaviour of self compacting concrete. *Construction and Building Materials*, 84, 103-110.
62. Meddah, M.S.; Ismail, M.A.; El-Gamal, S.; and Fitriani, H. (2018). Performances evaluation of binary concrete designed with silica fume and metakaolin. *Construction and Building Materials*, 166, 400-412.
63. Specification, I.S. (1984). No. 5/1984, *Portland Cement*. Central Organization for Standardization & Quality Control (COSQC) (1st ed.). Baghdad: Iraq.

64. Specification, S. (2014). *ASTM C1240, Standard specification for silica fume used in cementitious mixtures*, West Conshohocken (2nd ed.). New York: USA.
65. Mozan, S.J.; and Khalil, W.I. (2016). Properties of high strength lightweight aggregate concrete paving bricks. *Diyala Journal of Engineering Sciences*, 9(3), 120-132.
66. Shubbar, A.A.; Jafer, H.; Dulaimi, A.; Hashim, K.; Atherton, W.; and Sadique, M. (2018). The development of a low carbon binder produced from the ternary blending of cement, ground granulated blast furnace slag and high calcium fly ash: An experimental and statistical approach. *Construction and Building Materials*, 187, 1051-1060.
67. Specification, I.S. (1984). *No.45, Aggregate from natural sources for concrete and building construction* (1st ed.). Baghdad: Iraq.
68. Specification, S. (2013). *ASTM C494/C494m-13, Standard Specification for Chemical Admixtures for Concrete*, West Conshohocken (2nd ed.). New York: USA.
69. Specification, S. (2013). *ASTM C109/C109m-13e1, Standard test method for compressive strength of hydraulic cement mortars (Using 2-in. or [50-mm] cube specimens)* (2nd ed.). New York: USA.
70. Specification, S. (2013). *ASTM C1437-13, Standard Test Method for Flow of Hydraulic Cement Mortar*, West Conshohocken (2nd ed.). New York: USA.
71. Specification, S. (2013). *ASTM C642, Standard test method for density, absorption, and voids in hardened concrete*, West Conshohocken (2nd ed.). New York: USA.
72. Siddique, R. (2011). Utilization of silica fume in concrete: Review of hardened properties. *Resources, Conservation and Recycling*, 55(11), 923-932.
73. Zhang, Z.; Zhang, B.; and Yan, P. (2016). Comparative study of effect of raw and densified silica fume in the paste, mortar and concrete. *Construction and Building Materials*, 105(82-93).
74. Sanjuán, M.Á.; Argiz, C.; Gálvez, J.C.; and Moragues, A. (2015). Effect of silica fume fineness on the improvement of Portland cement strength performance. *Construction and Building Materials*, 96, 55-64.
75. Castro, J.; Bentz, D.; and Weiss, J. (2011). Effect of sample conditioning on the water absorption of concrete. *Cement and Concrete Composites*, 33(8), 805-813.
76. Wongkeo, W.; Thongsanitgarn, P.; Ngamjarujana, A.; and Chaipanich, A. (2014). Compressive strength and chloride resistance of self-compacting concrete containing high level fly ash and silica fume. *Materials & Design*, 64, 261-269.