



LJMU Research Online

Hashim, KS, Ewadh, HM, Muhsin, AA, Zubaidi, SL, Kot, P, Muradov, M, Aljefery, M and Al Khaddar, RM

Phosphate removal from water using bottom ash: Adsorption performance, coexisting anions and modelling studies

<http://researchonline.ljmu.ac.uk/id/eprint/14145/>

Article

Citation (please note it is advisable to refer to the publisher's version if you intend to cite from this work)

Hashim, KS, Ewadh, HM, Muhsin, AA, Zubaidi, SL, Kot, P, Muradov, M, Aljefery, M and Al Khaddar, RM (2020) Phosphate removal from water using bottom ash: Adsorption performance, coexisting anions and modelling studies. Water Science and Technology. ISSN 0273-1223

LJMU has developed [LJMU Research Online](#) for users to access the research output of the University more effectively. Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Users may download and/or print one copy of any article(s) in LJMU Research Online to facilitate their private study or for non-commercial research. You may not engage in further distribution of the material or use it for any profit-making activities or any commercial gain.

The version presented here may differ from the published version or from the version of the record. Please see the repository URL above for details on accessing the published version and note that access may require a subscription.

For more information please contact researchonline@ljmu.ac.uk

<http://researchonline.ljmu.ac.uk/>

Phosphate removal from water using bottom ash: Adsorption performance, coexisting anions and modelling studies

Khalid S. Hashim^{1,2,*}, Hind Mufeed Ewadh³, Adnan A. Muhsin⁴, Salah L. Zubaidi⁵, Patryk Kot¹, Magomed Muradov¹, Mohammed Aljefery¹ and Rafid Al-Khaddar¹

¹ Built Environment and Sustainable Technologies (BEST) Research Institute, Liverpool John Moores University, Liverpool, L3 3AF, UK

² Faculty of Engineering, University of Babylon, Hilla, 5200, Iraq

³ Environmental Research and Studies Center, University of Babylon, Hilla, 52001, Iraq

⁴ Al-Furat Al-Awsat Technical University, Al-Mussaib Technical Institute, Babylon, 51009, Iraq

⁵ Department of Civil Engineering, Wasit University, Wasit, 51001, Iraq

*Corresponding author: k.s.hashim@ljamu.ac.uk

Abstract

Phosphate in freshwater possesses significant effects on both quality of water and human health. Hence, many treatment methods were used to remove phosphate from water/wastewaters, such as biological and electrochemical methods. Recent researches demonstrated that adsorption approaches are convenient solutions for water/wastewater remediation from phosphate. Thus, the present study employs industrial by-products (bottom ash (BA)), as a cost-effective and eco-friendly alternative, to remediate water from phosphate in the presence of competitor ions (humic acid). This study was initiated by characterising the chemical and physical properties of the BA, sample, then the Central Composite Design (CCD) was utilised to design the required batch experiments and to model the influence of solution temperature (ST), humic acid concentration (HAC), pH of the solution (PoS) and doses of adsorbent (DoA) on the performance of the BA. Langmuir model was utilised to assess the adsorption process. The outcomes of this study evidenced that the BA removed 83.8% of 5.0 mg/l of phosphates at ST, HAC, PoS and DoA 35 °C, 20 mg/L, 5 and 55 g/L, respectively. The isotherm study indicated a good affinity between BA and phosphate. Additionally, the developed model, using the CCD, reliably simulated the removal of phosphates using BA ($R^2= 0.99$).

Keywords: Phosphate; furnace bottom ash; adsorption; industrial by-products.

1. Introduction

The agricultural industry has witnessed substantial changes during the last half-century to meet the soaring demands for foods and fibers (Zalidis *et al.* 2002; Alwash 2017), which results in a substantial deterioration of freshwater sources (Withers *et al.* 2014; Zhao *et al.* 2015; Omran *et al.* 2019). For instance, agriculture contributes to 60% of nitrate and 25% of phosphate in the freshwater sources in the United Kingdom, and about 75% of sediments contaminating freshwater sources worldwide (Holden *et al.* 2015). In addition, it results in huge economic losses, for instance, the eutrophication of freshwaters in England and Wales due to the occurrence of phosphorus, which resulted in annual losses of \$105,000,000 and \$160,000,000, respectively. Generally, there are two main ways to transport phosphate from agricultural landscapes to the sources of freshwaters; surface runoffs and sub-surface flows (Sellner 2016). It was believed that the surface runoffs are the main way for transporting phosphate from farms to the receiving water bodies, however recent studies have evidenced that sub-surface flow is the predominant way of phosphate transportation from farms to the sources of freshwaters (King *et al.* 2015). For example, King *et al.* (2015) conducted a study for 8 years to estimate the contribution of sub-surface flow to the total phosphate in central Ohio; the results of their study proved that sub-surface flow is responsible for 48% of the total phosphate in that area, and also proved that $\geq 90\%$ of the measured concentrations were ≥ 0.02 mg/L. It must be mentioned that the agricultural activities are not the only origin of phosphate in the aquatic environment; considerable concentrations of phosphate could be found in the domestics and industrial effluents (Alwash 2017).

To mitigate phosphate discharging into the sources of freshwaters and to avoid further deterioration of freshwater sources and phosphate-related health problems, effective treatment approaches must be used to remove phosphate from effluents. To solve this dilemma, the specialists have suggested a number of complex or simple technologies, such as nanomaterial-based methods, biological reactors and wetlands, electrochemical reactors, artificial absorbents and natural absorbents (Dai & Pan 2014; Park *et al.* 2015; Alwash 2017; Kumar *et al.* 2019). Adsorption technology, which bases on the sorption of phosphate on low-cost artificial or natural and by-products absorbents, has been recently recognized as a promising method for remediation of water not only from phosphate but also from a broad-spectrum of contaminants. For instance, by-products of steel and iron factories, limestone, calcite, zeolites, exfoliated vermiculites, ferric hydroxide, nanoparticles of different materials, and activated carbons (derived from artificial or natural origins) were employed in the literature to remediate waters from phosphate (Alwash 2017; Kumar *et al.* 2019). Generally, any material with rich content of aluminium, magnesium, calcium, or/and iron oxide is favourable in the phosphate adsorption process as the oxides have the capacity to provide cations for phosphate to react with. The latter reaction, between phosphate and cations, yields insoluble compounds, which could be easily separated from the solutions being treated (Sellner 2016). A promising phosphate sorption material is the by-products of the coal burning process (in furnaces) as the latter is usually rich with one or more of the mentioned oxides (Kirk *et al.* 2003). By-products of the coal burning are divided

1 into two types; the first one is very small in size and has a lightweight, thus it escapes the combustion
2 chamber through the chimney, and is known as fly ash. While the second type, which is known as
3 bottom ash (BA), mainly consists of inorganic and non-combustible particles that remain in the bottom
4 of the combustion chamber due to their relatively heavyweight and large sizes (Kirk *et al.* 2003).
5 Although BA is rich in iron and aluminium oxides, the majority of BA is wasted in landfills (Hjelmar *et*
6 *al.* 2010) that requires expensive land and transportation investments. However, due to the attractive
7 chemical composition and free availability of BA, some trials have been made to recycle it in some
8 applications, such as the concrete industry (Zhang & Poon 2015; Shubbar *et al.* 2018). However, to
9 the best of the authors' knowledge, fresh BA from power plants was not used in water treatment yet.
10 Few trials were made to use the nano-powder of BA in water treatment (Alwash 2017), which have
11 limited applications due to the high production cost (production of nanopowder) and the safety
12 concerns (Tyagi *et al.* 2018).

13 In the present study, the BA has been utilised as an economically efficient adsorbent for phosphate.
14 The selection of the BA here is due to two main reasons; firstly, because the BA is rich in iron
15 aluminium oxides (as stated in the results section of this study) that gives it a good potential capacity
16 for phosphate sorption. Secondly, because the BA itself is classified as industrial by-products that are
17 environmentally harmful and it usually requires expensive management plans (Jamaludin *et al.* 2019).
18 Thus, utilising this by-product in water treatment is environmentally and economically beneficial. To
19 have a preliminary decision about the applicability of AB for remediation of water from phosphate;
20 several batch experiments were commenced taken into accounts the influences of solution
21 temperature (ST), humic acid concentration (HAC), pH of the solution (PoS) and doses of adsorbent
22 (DoA). It noteworthy to mention that humic acid has been used here to mimic the effects of competitor
23 ions in the field works. Humic acid was used as a competitor ions model here due to its wide
24 occurrence in the freshwaters and wastewaters (Han *et al.* 2017).

25 **2. Methodology**

26 **2.1. Characterization of the BA sample**

27 The sample of BA was obtained from a local power station in England, UK. The key chemical and
28 physical properties of the collected BA sample were examined before applying it for phosphate
29 removal from water; the studied properties were the grain size distribution, coefficient of uniformity
30 (CU), coefficient of gradation (CG), surface area, specific gravity, and chemical composition.

31 Sieve analysis was used to measure the grain size distribution; a measured weight of BA, 0.25 kg,
32 has been sieved using a set of sieves (No.6, No.10, No.16, and No.30 top-to-bottom) using a bench-
33 scale shaker (model: Impact SV-003). The retained weight of BA on each sieve was measured to
34 estimate the grain size distribution. The measured weights were used to calculate the CU (Eq.1) and
35 CG (Eq.2); well-graded samples have $CU > 4.0$ and CG in the range 1-3 (Viswanadham 2016).

1
$$CU = \frac{d_{60}}{d_{10}} \quad (1)$$

2
$$CG = \frac{d_{30}^2}{d_{10} \times d_{60}} \quad (2)$$

3 where d_{60} is the grain size that 60 percent of other grains are finer than it, d_{10} is the grain size that 10
4 percent of other grains are finer than it, and similarly d_{30} is the grain size that 30 percent of other
5 grains are finer than it.

6 The specific surface area of BA particles has been measured as it determines the number of actives
7 sites, which directly affects the adsorption efficiency. In the present study, a surface area analyser
8 (Quantachrome Nova-2000) was employed to determine the specific surface area of the BA particles.
9 In this process, the BA sample was outgassed with pure N_2 for 12.0 hours at a temperature of 300 °C
10 (Boonamnuayvitaya *et al.* 2005). Then the recorded data was applied to equations 3 and 4 to
11 calculated the specific surface area of the BA sample (Gregg & Sing 1982).

12
$$\text{Surface area} = \frac{X_m \times L_{av} \times A_m}{M_v} \quad (3)$$

13
$$\text{Specific surface area} = \frac{\text{Surface area}}{\text{weight of sample}} \quad (4)$$

14 Where X_m , L_{av} , A_m , and M_v are the monolayer capacity, Avogadro's number, the cross-sectional area
15 of the adsorbent, and the molar volume, respectively. The chemical composition of BA was analysed
16 using an X-ray fluorescence analyser (Shimadzu EDX-720). This test was run to calculate the
17 concentrations of oxides and trace elements in the BA sample.

18 **2.2. Batch experiments**

19 A suitable amount of mono-potassium phosphate, 7.17 mg, was dissolved in deionized water to
20 produce 5 mg/L phosphate solution, which was polluted with different concentrations of humic acid
21 (10 to 50 mg/L), as competitor ions, using the suitable amount of humic acid sodium salt. It is
22 noteworthy to mention that humic acid has been chosen as a model for competitor ions as it broadly
23 occurs in freshwaters (Han *et al.* 2017). The simulated phosphate-humic acid solution was treated
24 BA.

25 For each experiment, BA and phosphate-humic acid solution were mixed at different ratios (40 to 60
26 g/L), then the mixture was shaken, using a bench-top shaking Incubator (Model: Labnet-222DS) at
27 speed of 100 rpm for 24 hours (Sellner 2016). The residual phosphate concentration in solution was
28 measured by filtering a few millimetres at a 0.45µm filter and analysed using standard phosphate
29 cuvette tests (LCK-349 and 350) and a spectrophotometer (DR-2800). It is noteworthy to mention that
30 to measure the concentration of humic acid using the spectrophotometer, a calibration curve was first
31 developed for concentration range 0 to 50 mg/L. The equilibrium adsorption capacity, q_e (mg/g), was
32 measured as follows (Sellner 2016):

$$1 \quad q_e \left(\frac{\text{mg}}{\text{g}} \right) = \frac{V(C_i - C_e)}{m} \quad (5)$$

$$2 \quad \text{Removal efficiency (Re\%)} = \frac{(C_i - C_e)}{C_i} \times 100\% \quad (6)$$

3 where C_i and C_e are the initial and equilibrium phosphate concentrations (mg/L), respectively, m is the
4 amount of BA (grams), V is the volume of phosphate-humic acid solution (litters).

5 **2.3. Adsorption isotherm**

6 It is very essential, in the adsorption studies, to assess the relationship between the adsorbed and
7 aqueous concentrations at the equilibrium status. Many isotherm models could be used to assess this
8 relationship, such as Langmuir and Freundlich models (Alwash 2017). In the present study, the
9 Langmuir model, Eq. 7, has been applied to assess the relationship between the adsorbed and
10 aqueous concentrations of phosphate not only because this model is the most widely used one, but
11 also it delivers the required parameters to determine the separation factor (R_L), which is represented
12 by Eq.8 (Al-Othman *et al.* 2012). The latter gives a direct assessment for the affinity between the
13 absorbate and absorbent; the adsorption process is unfavourable, linear, favourable, or irreversible
14 when $R_L > 1$, $R_L = 1$, $1 > R_L > 0$, and $R_L = 0$, respectively (Dada *et al.* 2012).

$$15 \quad \frac{C_e}{q_e} = \frac{1}{Q_o \times b} + \frac{C_e}{Q_o} \quad (7)$$

$$16 \quad R_L = \frac{1}{1 + b \times C_i} \quad (8)$$

17 where Q_o and b represents the theoretical mono-layer adsorption (mg/g) and the energy of adsorption
18 (L/mg), respectively. The values of Q_o and b can be obtained from the plot of the Langmuir model
19 (C_e/q_e against C_e); Q_o and b are obtained from the slopes and intercepts of the mentioned plot,
20 respectively. In the present study, the Langmuir model was performed by mixing 100 ml of phosphate
21 solution with different amounts of BA (1.5 to 6.5 g/L), in airtight containers, and shaken for 24 hours at
22 speed of 100 rpm to reach the equilibrium status. The results were plotted to get the required
23 information to calculate R_L .

24 **2.4. Optimisation and modelling of phosphate adsorption**

25 The adsorption process was optimised using Central Composite Design (CCD) which is a member of
26 the Response Surface Methodology. The CCD has been performed using the Minitab package
27 (version 19), and the optimisation process covered the influences of solution temperature (ST), humic
28 acid concentration (HAC), pH of the solution (PoS), and doses of adsorbent (DoA) on the adsorption
29 process. The studied ranges of the PoS, ST, HAC, and DoA are tabulated in Table 1. The incubator
30 was used to adjust the ST to the desired value (20-40 °C), while the PoS was adjusted to the range of

1 3-11 using NaOH or HCl solution. Additionally, a regression analysis was performed to assess the
 2 significance of each one of the studied parameters in the adsorption of phosphate on the BA particles.

3 **Table 1:** Ranges of the studied parameters.

Parameter	Unit	Ranges				
		-2	-1	0	+1	+2
ST	°C	20	25	30	35	40
HAC	mg/l	10	20	30	40	50
PoS	Unitless	3	5	7	9	11
DoA	g/L	25	35	45	55	65

4 Performing CCD yielded 31 experimental runs, see Table 2, which are essential to attain the optimum
 5 performance of the BA filter in terms of phosphate removal under the mentioned conditions, and also
 6 this number of experiments are necessary to develop a simulation model for phosphate removal by
 7 BA.

8 **Table 2:** Experimental runs according to CCD.

Runs	ST	HAC	PoS	DoA	Runs	ST	HAC	PoS	DoA
1	30	30	7	45	17	35	20	9	55
2	30	30	7	45	18	30	30	7	65
3	25	40	9	55	19	25	40	5	35
4	35	40	5	55	20	25	40	9	35
5	30	30	7	45	21	35	20	9	35
6	35	20	5	35	22	35	20	5	55
7	35	40	5	35	23	30	30	3	45
8	30	30	7	25	24	30	50	7	45
9	20	30	7	45	25	30	30	7	45
10	25	20	9	35	26	30	30	7	45
11	35	40	9	55	27	35	40	9	35
12	30	30	7	45	28	30	30	7	45
13	40	30	7	45	29	30	30	11	45
14	25	20	5	55	30	25	40	5	55
15	30	10	7	45	31	25	20	9	55
16	25	20	5	35					

9 3. Results and discussion

10 3.1. Characterization of the BA sample

11 As it was mentioned above, the physical and chemical properties of the BA sample determine its
 12 suitability for the adsorption process. Therefore, the chemical composition and physical properties
 13 (grain size distribution, CU, CG, surface area, and specific gravity) have been examined.

14 The chemical composition analyses of BA have revealed considerable concentrations of aluminium,
 15 iron, calcium, and magnesium oxides, which are favourable for phosphate removal. According to the
 16 listed results in Table 3, about 18.287% of the chemical composition of BA is consists of the
 17 mentioned oxides, which confirms that this by-product is suitable for phosphate adsorption.

18

1

Table 3: Chemical composition of BA.

Oxide	Percentage	Oxide	Percentage
Al ₂ O ₃	9.953	CHO	60.381
Fe ₂ O ₃	6.321	BaO	0.193
CaO	1.301	SO ₃	0.191
MgO	0.712	SrO	0.052
SiO ₂	19.301	CO ₂ O ₃	0.0162
K ₂ O	0.753	ZrO ₂	0.016
TiO ₂	0.272	MnO	0.038

Other trace elements represent less than 0.005 of the chemical composition of BA

2 Table 4 shows the physical properties of BA, which confirm that the physical properties of the BA
 3 sample are suitable for the adsorption process; the BA sample is well-graded as its CU was more
 4 than 4.0 and its CG was in the range of 1-3 (Viswanadham 2016). Additionally, the specific gravity of
 5 BA is bigger than that of water, which means it will not float during the adsorption process.

6

Table 4: Physical properties of BA.

Parameter	CU	CG	Specific gravity	Surface area (m ² /g)
Value	5.450	1.369	1.285	5

7 3.2. Batch experiments

8 Phosphate removal experiments have been carried out according to the presented experimental
 9 design in Table 2. The obtained results are presented in Table 5 and Figure 1. According to the
 10 obtained results, maintaining the PoS in the acidic range resulted in better removal of phosphate in
 11 comparison with neutral and alkaline ranges. For instance, the removal of phosphate decreased from
 12 68.4% to 59.9% and 32.7% as the PoS increased from 3 to 7 and 11, respectively, when the ST,
 13 HAC, and DoA were kept constant at 30 °C, 30 mg/L, and 45 mg/L, respectively. The lower phosphate
 14 adsorption at the alkaline medium is probably because the higher PoS, the absorbent particles carry
 15 more negative charges, which intensifies the repulsion between the absorbent particles and
 16 negatively charged phosphate ions (Alwash 2017). Other researchers attributed the lower phosphate
 17 adsorption at the alkaline medium to the increase in adsorption of OH⁻ ions onto the absorbent,
 18 decreasing the availability of adsorption sites for phosphate (Sellner 2016). The literature, (Sellner
 19 2016; Alwash 2017) demonstrated similar effects of PoS on phosphate removal by adsorption
 20 method.

21

22

23

24

1

Table 5: Removal of phosphate using BA.

Runs	ST	HAC	PoS	DoA	Re. (%)	Runs	ST	HAC	PoS	DoA	Re. (%)
1	30	30	7	45	60.3	17	35	20	9	55	72.8
2	30	30	7	45	60.0	18	30	30	7	65	77.4
3	25	40	9	55	54.2	19	25	40	5	35	47.6
4	35	40	5	55	72.7	20	25	40	9	35	22.4
5	30	30	7	45	59.9	21	35	20	9	35	36.1
6	35	20	5	35	57.3	22	35	20	5	55	83.8
7	35	40	5	35	48.4	23	30	30	3	45	68.4
8	30	30	7	25	17.1	24	30	50	7	45	55.2
9	20	30	7	45	57.4	25	30	30	7	45	60.0
10	25	20	9	35	35.3	26	30	30	7	45	59.9
11	35	40	9	55	55.8	27	35	40	9	35	24.1
12	30	30	7	45	59.8	28	30	30	7	45	60.1
13	40	30	7	45	57.8	29	30	30	11	45	32.7
14	25	20	5	55	82.1	30	25	40	5	55	71.2
15	30	10	7	45	78.7	31	25	20	9	55	71.4
16	25	20	5	35	56.4						

2

3

4

5

6

7

8


9

10

11

12

13

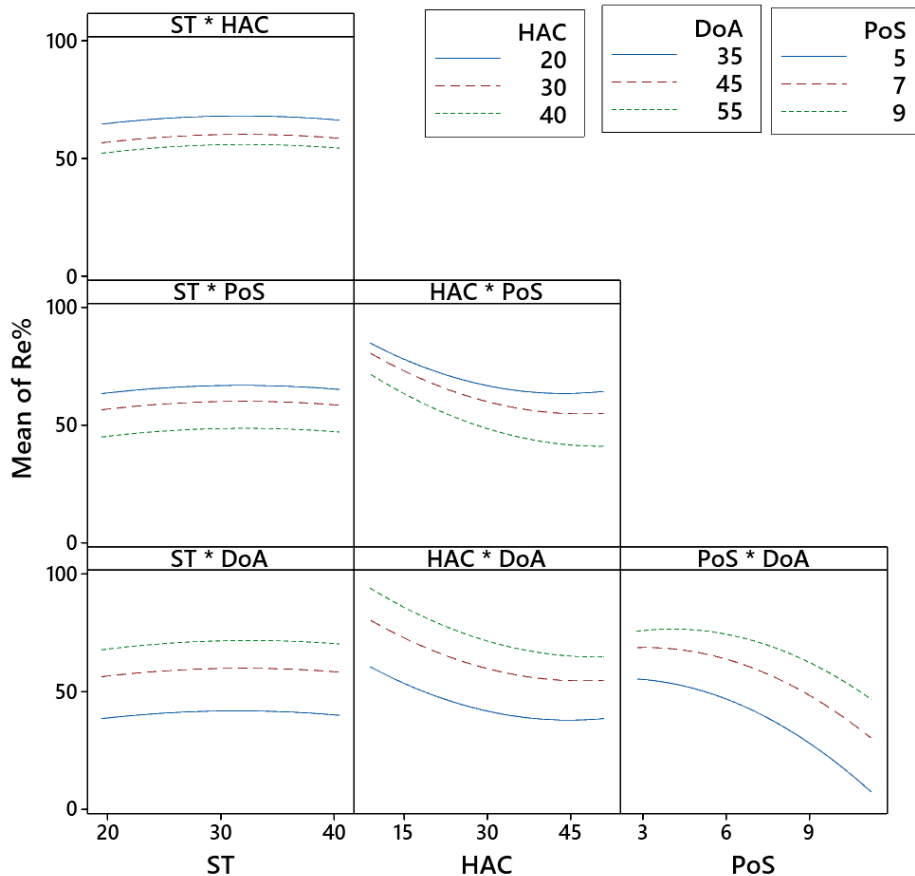

14

Figure 1: Interaction between phosphate removal and ST, HAC, PoS and DoA.

15

16

17

18

The results obtained from the experimental work evidenced that the occurrence of coexisting ion, humic acid, exerted negative impacts on the adsorption of phosphate by BA particles, especially at high concentrations. It can be obviously seen from the results of Table 5 and Figure 1 that the increasing the HAC from 10 to 50 mg/L shrank the removal of phosphate by about 24%, when the ST,

1 PoS, and DoA were kept constant at 30 °C, 7 and 45 mg/L, respectively. According to the literature,
2 there are three possible reasons from this shrank in phosphate removal with the increase of HAC; i)
3 the competitive adsorption of humic acid and phosphate onto the surfaces of BA particles; ii) the
4 accumulation of organic matter on the surface of the adsorbent weakens or changes the surface
5 charge of adsorbent that minimises the electrostatic attraction; and iii) organic matter could delay or
6 inhibit the chemical reactions between phosphate and aluminium and iron oxides (Borggaard *et al.*
7 2005; Sellner 2016; Amini *et al.* 2020). The literature showed similar effects of humic acid on
8 phosphate adsorption onto different types of adsorbents, such as iron oxides (Weng *et al.* 2012).

9 Solution temperature (ST) has a substantial role in the adsorption process at liquid-solid interfaces as
10 it determines the driving force of phosphate ions onto the surfaces of the adsorbents, and it also
11 affects the energy barriers of reactions between the adsorbents and the adsorbates (Liu *et al.* 2011).
12 Therefore, the effects of ST on phosphate uptake by the BA particles have been examined at several
13 temperature levels, ranging from 20 to 40°C. According to the results of Table 5 and Figure 1, the
14 uptake capacity of BA for phosphate is positively influenced by the increase of ST to a certain limit; an
15 increase in the uptake of phosphate in ST range of 20 to 35 °C, but a slight decrease was noticed in
16 the uptake of phosphate when ST increased to 40 °C when the HAC, PoS, and DoA were kept
17 constant at 30 mg/L, 7 and 45 mg/L, respectively. For example, the removal of phosphate increased
18 from about 57% to 60% as the ST increased from 20 to 30 °C, respectively. However, increasing the
19 ST from 30 to 40 °C decreased the removal of phosphate from 60% to about 58%, respectively.
20 According to previous studies, there are several reasons behind the increase in the uptake of
21 phosphate with the increase of ST; increasing the bulk temperature expands the pore size on the
22 surface of adsorbents that increases the adsorption capacity (Alwash 2017). Another reason is the
23 increase of ST maximises the driving force of phosphate ions onto the surfaces of the adsorbents,
24 and it also minimises the energy barriers of reactions between the adsorbents and the adsorbates,
25 which enhances the removal of phosphate (Liu *et al.* 2011). Additionally, some researchers claimed
26 that increasing the ST could increase the solubility of iron and calcium oxides (from the adsorbents),
27 which enhances the phosphate precipitation (Mezenner & Bensmaili 2009). Higher temperatures
28 increase the relative motion of ions, which helps ions to escape from the adsorption sites (Xu *et al.*
29 2009).

30 The last examined parameter, in this study, was the dose of adsorbent (DoS). The results obtained
31 from the commenced experiments proved that the DoS substantially affect the removal of phosphate
32 by BA particles. For instance, the removal of phosphate was increased from the vicinity of 56% to the
33 vicinity of 82% as the DoS increased from 35 to 55 mg/L, respectively, when the ST, HAC, and PoS
34 were kept constant at 25 °C, 20 mg/L and 5, respectively. With increasing DoA, a larger number of
35 active adsorption sites are available for phosphate adsorption, which enhances the removal efficiency
36 (Xu *et al.* 2009).

1 In terms of the removal mechanism of phosphate from water using the BA particles, there are three
2 main mechanisms. Firstly, the high content of SiO₂ (about 20% of the chemical composition) indicates
3 that the physical adsorption of phosphate because the presence of silicon results in a microporous
4 structure of the material, which in turn increases the physical adsorption of phosphate (Zhou *et al.*
5 2019). Secondly, the presence of aluminium and iron oxides in the structure of BA promotes the
6 chemisorption of phosphate at the active sites on the surface of BA particles (Yan *et al.* 2010). It
7 should be mentioned that the SiO₂ plays an important role in the chemisorption of phosphate as it
8 increases the surface area of the adsorbent, which in turn enhances subjected are for the chemical
9 reactions between phosphate and aluminium and iron oxides. Chemical precipitation of phosphate is
10 the third predominant separation path due to the presence of calcium in the BA, which acts to
11 precipitate phosphate (Zhou *et al.* 2019).

12 In summary, according to the results obtained from this study, the lowest adsorption of phosphate,
13 17.1%, was noticed at the lowest DoA (25 mg/L) and ST, HAC, and PoS of 30 °C, 30 mg/L, and 7,
14 respectively. While the best adsorption of phosphate (83.8%) was noticed at the highest DoA (55
15 mg/L) and ST, HAC, and PoS of 35 °C, 20 mg/L, and 5, respectively.

16 A regression analysis was performed to assess the significance of each one of the studied
17 parameters in the adsorption of phosphate on the BA particles. The relative significances of the
18 studied parameters, according to the outcomes of regression analysis, follow the order: DoA > PoS >
19 HAC > ST, which means the DoA plays the most significant role in the adsorption of phosphate on the
20 BA particles, followed by the PoS and HAC and ST.

21 **3.3. Adsorption isotherm**

22 As it was mentioned above, assessment of the relationship between the adsorbed and aqueous
23 concentrations is a basic step in the adsorption studies. Thus, the Langmuir model has been
24 performed, in the present study, to assess the relationship between the adsorbed and aqueous
25 concentrations of phosphate. Additionally, the separation factor has been calculated to evaluate the
26 affinity between the phosphate and BA particles. Langmuir isotherm constants, Q_o and b , have been
27 calculated by plotting C_e/q_e against C_e , as depicted in Figure 2. The obtained values of Q_o and b were
28 6.522 (mg/g) and 0.14 (L/mg), respectively.

29 According to Eq.8 and the calculated Langmuir isotherm constant, the R_L value for the adsorption of
30 phosphate on the BA particles was 0.417, which confirmed that the adsorption of phosphate on BA
31 particles was a favourable adsorption (Dada *et al.* 2012).

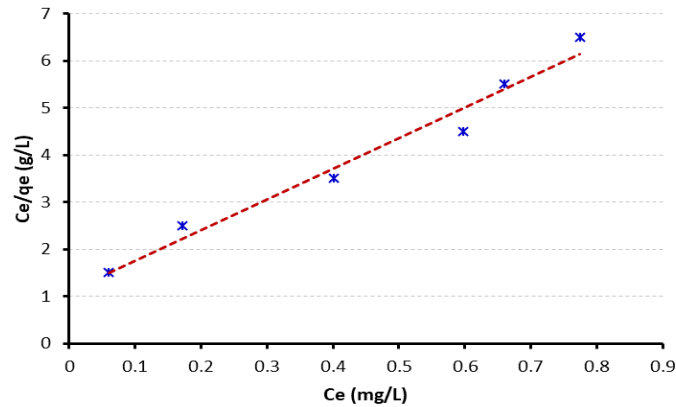


Figure 2: Langmuir isotherm for phosphate adsorption on BA particles.

1 A glance on the outcomes of the present study could reveal that the present method has an edge
 2 over many of commonly used methods for phosphate removal because it does not require a long
 3 treatment time, it does not produce significant volumes of sludge, it helps to recycle waste in an eco-
 4 friendly way, and it does not deplete the natural resources. For instance, the literature shows that
 5 biological reactors are one of the commonly used methods for phosphate removal, and they enjoy
 6 good removal efficiency that could reach as high as 99% (Li *et al.* 2016). However, the biological
 7 methods require long treatment time, produce high volumes of sludge with high moisture content that
 8 requires expensive management strategies, which negatively influence its cost-effectiveness. In
 9 addition, biological reactors require precise and continuous monitoring to avoid the death of the
 10 bacteria (Camcioğlu *et al.* 2019). In terms of advanced phosphate treatment methods, recent studies
 11 employed the nanomaterials, such as nano-alumina, to achieve rapid and efficient phosphate removal
 12 from solutions. Although the nanomaterials demonstrated efficient removal of phosphate from
 13 solutions, the high cost of the nanomaterials and the possibility of releasing nanoparticles into the
 14 water being treated (toxicity) are the main limitations for this type of treatment methods (Tyagi *et al.*
 15 2018).

16 **3.4. Modelling of phosphate adsorption on BA particle**

17 The observed removals of phosphate on BA particles, Table 5, have been fed to CCD to yield a
 18 simulation equation that could be used, in future studies, to reproduce the removal of phosphate on
 19 BA particles without the need for commencing laboratory-based experiments. Thus, such simulation
 20 equations save both time and cost of tests. The obtained simulation equation is shown in Eq.9.

$$\begin{aligned}
 \text{Re\%} = & -40.79 + 1.31 \times \text{ST} - 0.887 \times \text{HAC} + 0.246 \times \text{PoS} + 3.724 \times \text{DoA} - 0.02308 \times \text{ST}^2 + 0.0176 \times \text{HAC}^2 - \\
 & 0.5849 \times \text{PoS}^2 - 0.03165 \times \text{DoA}^2 + 0.001 \times \text{ST} \times \text{HAC} + 0.0037 \times \text{ST} \times \text{PoS} + 0.0025 \times \text{ST} \times \text{DoA} - \\
 & 0.06062 \times \text{HAC} \times \text{PoS} - 0.0085 \times \text{HAC} \times \text{DoA} + 0.11313 \times \text{PoS} \times \text{DoA}
 \end{aligned}
 \tag{9}$$

21 It is noteworthy to highlight that the negative signs before the parameters or the combinations of
 22 parameters in Eq.7 are to highlight the negative impact of these parameters or combinations of
 23 parameters on the adsorption of phosphate on the BA particles, while the positive signs indicate the
 24 positive impacts.

1 In fact, it is not necessary that every single parameter, in Eq.7, makes a statistically significant
 2 contribution to the suggested model, where some of the parameters can be omitted from the
 3 suggested model due to their ignorable contribution (Pallant 2005; Hashim *et al.* 2017). The
 4 contribution of each parameter to the suggested model was assessed by determining its statistical
 5 significance (p-value). This parameter indicates whether this parameter makes a statistically
 6 significant contribution to the model or not; any parameter with a p-value less than 0.05 makes a
 7 significant unique contribution to the multiple regression model, while any parameter with a p-value
 8 more than 0.05 can be omitted from the model as it does not play a significant role (Pallant 2005;
 9 Hashim *et al.* 2017). According to the results of Table 6, three parameters, namely (ST×HAC),
 10 (ST×PoS), and (ST×DoA), can be omitted from the model because their p-values are more than 0.05.
 11 Thus, the new formula of the suggested model is:

$$\text{Re\%} = -40.79 + 1.31 \times \text{ST} - 0.887 \times \text{HAC} + 0.246 \times \text{PoS} + 3.724 \times \text{DoA} - 0.02308 \times \text{ST}^2 + 0.0176 \times \text{HAC}^2 - 0.5849 \times \text{PoS}^2 - 0.03165 \times \text{DoA}^2 - 0.06062 \times \text{HAC} \times \text{PoS} - 0.0085 \times \text{HAC} \times \text{DoA} + 0.11313 \times \text{PoS} \times \text{DoA} \quad (10)$$

12 The normal probability plot and versus order plots of the suggested model are shown in Figure 3.

13 **Table 6:** Analysis of variance.

Source	Degrees of Freedom	Sequential sum of squares	Contribution	Adjusted sum of squares	Adjusted mean squares	P-Value
Model	14	8870.63	99.94%	8870.63	633.617	0.000
Linear	4	8196.06	92.34%	260.56	65.140	0.000
ST	1	5.23	0.06%	5.59	5.589	0.001
HAC	1	885.73	9.98%	14.09	14.091	0.000
PoS	1	1994.73	22.47%	0.04	0.041	0.007
DoA	1	5310.38	59.83%	214.90	214.902	0.000
Square	4	557.27	6.28%	557.27	139.318	0.000
ST*ST	1	1.82	0.02%	9.52	9.523	0.000
HAC*HAC	1	153.05	1.72%	88.62	88.620	0.000
PoS*PoS	1	116.03	1.31%	156.52	156.523	0.000
DoA*DoA	1	286.37	3.23%	286.37	286.375	0.000
2-Way Interaction	6	117.30	1.32%	117.30	19.550	0.000
ST*HAC	1	0.04	0.00%	0.04	0.040	0.727
ST*PoS	1	0.02	0.00%	0.02	0.023	0.794
ST*DoA	1	0.25	0.00%	0.25	0.250	0.388
HAC*PoS	1	23.52	0.27%	23.52	23.522	0.000
HAC*DoA	1	11.56	0.13%	11.56	11.560	0.000
PoS*DoA	1	81.90	0.92%	81.90	81.903	0.000
Error	16	5.08	0.06%	5.08	0.318	----
Lack-of-Fit	10	4.92	0.06%	4.92	0.492	0.001
Pure Error	6	0.16	0.00%	0.16	0.027	----
Total	30	8875.72	100.00%	----	----	----

14

15

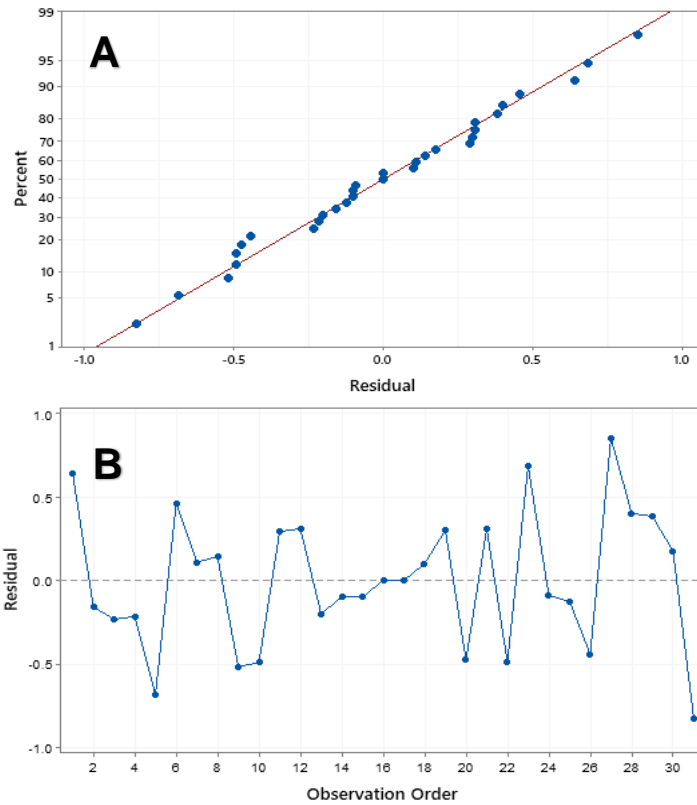


Figure 3: A) The normal probability plot, B) Versus order plot.

1 To validate the developed model, it has been used to predict the adsorption of phosphate on the BA
 2 particles under the stated conditions in Table 5. The predicted removals of phosphate have been
 3 compared with the observed removals, see Table 7. Additionally, the coefficient of determination (R^2),
 4 which an effective tool to assess the relationship between the predicted and observed phosphate
 5 removals, has been calculated by plotting the predicted phosphate removals against the observed
 6 removals, see Figure 4.

7

Table 7: Predicted and observed phosphate removals by BA particles.

Runs	Observed removal (%)	Predicted removal (%)	Runs	Observed removal (%)	Predicted removal (%)
1	57.4	53.38	17	60	59.99
2	22.4	22.54	18	60.1	59.99
3	35.3	35.53	19	60.3	59.99
4	47.6	47.81	20	68.4	68.88
5	54.2	54.86	21	77.4	77.08
6	56.4	55.94	22	78.7	79.19
7	71.2	71.08	23	24.1	23.40
8	71.4	71.24	24	36.1	36.19
9	82.1	82.61	25	48.4	48.52
10	17.1	17.59	26	55.8	56.22
11	32.7	32.39	27	57.3	56.45
12	55.2	54.88	28	72.7	72.29
13	59.8	59.99	29	72.8	72.40
14	59.9	59.99	30	83.8	83.62
15	59.9	59.99	31	57.8	58.62
16	60	59.99			

1 It can be seen from Table 7 that the observed removals of phosphate are in good agreement with the
2 predicted removals. Additionally, the calculated value of R^2 was 0.99, which means the simulation
3 model can reliably predict 99% of the effects of the studied parameters on phosphate removals by the
4 BA particles.

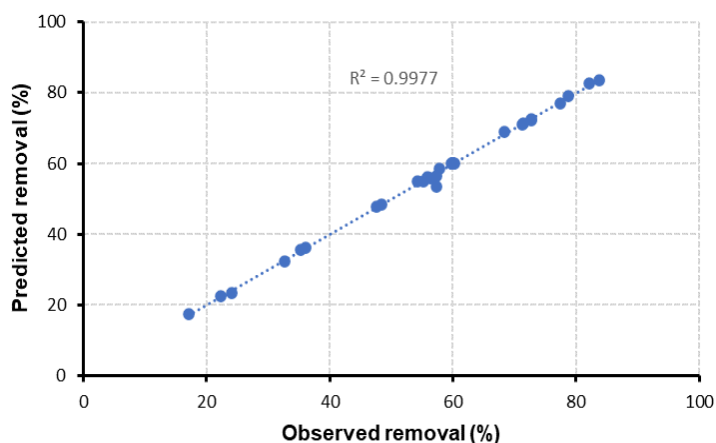


Figure 4: Linear fit of the predicted and observed phosphate removals.

5 4. Conclusions

6 The current study was devoted to investigate the applicability of industrial by-products, BA from power
7 plants, to remove phosphate from water in the presence of competitor ions. The investigation was
8 initiated by studying the chemical and physical characteristics of the BA to ensure that it has the
9 potential ability to remove phosphate, i.e., to check the content of iron and aluminium oxides and its
10 surface area and density. Then, its ability to remove phosphate was validated by commencing sets of
11 batch experiments under different conditions; including the DoA, PoS, ST and HAC. The kinetics of
12 the adsorption process was also investigated using the Langmuir isotherm model. The outcomes of
13 this study indicated that the BA sample contains considerable concentrations of iron, aluminium, and
14 manganese oxides, which have good ability to remove phosphate from solutions, and it was found
15 that the best performance of the BA particles could be attained in acidic solution, high dose of BA and
16 in normal to moderate temperature levels (up to 35 °C). It was also found that both high pH and/or
17 water temperatures negatively influenced the efficiency of the BA. Additionally, it was found that the
18 presence of humic acid substantially minimised the adsorption of phosphate due to the competition for
19 the adsorption sites. The adsorption isotherm study evidenced a high affinity between the BA particles
20 and phosphate. Finally, it was found that the CCD could be efficiently used to model phosphate
21 adsorption on BA.

22 Generally, the outcomes of the present study could be preliminary evidence about the suitability of the
23 BA particles, as economically efficient and eco-friendly adsorbent, for phosphate removal from water.
24 For future studies, BA could be used to remediate water from other common pollutants, such as

1 heavy metals and nitrates. Additionally, more studies should be commenced to develop adsorption
2 mediums from industrial or agricultural by-products.

3 **Acknowledgment:** The authors are grateful to the research team from Al-Furat Al-Awsat Technical
4 University and University of Babylon for carrying out the majority of the experiments during the
5 lockdown period in the UK.

6 **References**

- 7 Al-Othman Z. A., Ali R. and Naushad M. (2012). Hexavalent chromium removal from aqueous
8 medium by activated carbon prepared from peanut shell: adsorption kinetics, equilibrium and
9 thermodynamic studies. *Chemical Engineering Journal* **184**, 238-47.
- 10 Alwash R. S. M. (2017). *Treatment of Highly Polluted Water with Phosphate using BAPPP-*
11 *Nanoparticles*. MSc thesis, Environmental Engineering, MSc thesis, University of Technology,
12 Iraq.
- 13 Amini M., Antelo J., Fiol S. and Rahnemaie R. (2020). Modeling the effects of humic acid and anoxic
14 condition on phosphate adsorption onto goethite. *Chemosphere* **253**,1-10.
- 15 Boonamnuayvitaya V., Sae-ung S. and Tanthapanichakoon W. (2005). Preparation of activated
16 carbons from coffee residue for the adsorption of formaldehyde. *Separation and purification*
17 *Technology* **42**(2), 159-68.
- 18 Borggaard O. K., Raben-Lange B., Gimsing A. L. and Strobel B. W. (2005). Influence of humic
19 substances on phosphate adsorption by aluminium and iron oxides. *Geoderma* **127**(3-4), 270-
20 9.
- 21 Camcioğlu Ş., Özyurt B., Şengül S. and Hapoğlu H. (2019). Evaluation of Electro-Fenton Method on
22 Cheese Whey Treatment: Optimization Through Resonse Surface Methodology.
- 23 Dada A., Olalekan A., Olatunya A. and Dada O. (2012). Langmuir, Freundlich, Temkin and Dubinin–
24 Radushkevich isotherms studies of equilibrium sorption of Zn²⁺ unto phosphoric acid
25 modified rice husk. *IOSR Journal of Applied Chemistry* **3**(1), 38-45.
- 26 Dai L. and Pan G. (2014). The effects of red soil in removing phosphorus from water column and
27 reducing phosphorus release from sediment in Lake Taihu. *Water science and technology*
28 **69**(5), 1052-8.
- 29 Gregg S. and Sing K. (1982). Adsorption, surface area and porosity. Academic Press, London.
30 *Adsorption, surface area and porosity. 2nd ed. Academic Press, London., -.*
- 31 Han L., Xiao T., Tan Y. Z., Fane A. G. and Chew J. W. (2017). Contaminant rejection in the presence
32 of humic acid by membrane distillation for surface water treatment. *Journal of membrane*
33 *science* **541**, 291-9.
- 34 Hashim K. S., Shaw A., Al Khaddar R., Ortoneda Pedrola M. and Phipps D. (2017). Defluoridation of
35 drinking water using a new flow column-electrocoagulation reactor (FCER) - Experimental,
36 statistical, and economic approach. *Journal of environmental management* **197**, 80-8.
- 37 Hjelmar O., Johnson A. and Comans R. (2010). Incineration: Solid Residues. In: *Solid Waste*
38 *Technology and Management, Volume 1 and 2* Christensen TH (ed.), John Wiley & Sons, Ltd,
39 Chichester, UK.

- 1 Holden J., Haygarth P. M., MacDonald J., Jenkins A., Sapiets A., Orr H. G., Dunn N., Harris B.,
2 Pearson P. L. and McGonigle D. (2015). *Farming and Water 1: Agriculture's impacts on water*
3 *quality*, Global Food Security and The UK Water Partnership, UK.
- 4 Jamaludin S. S., Rani N. A. and Mohamad N. (2019). Investigation of water absorption and strength
5 performances on concrete bricks containing Malaysian thermal power plant coal bottom ash
6 (CBA). *Journal of Physics: Conference Series* **1349**, 1-6.
- 7 King K. W., Williams M. R. and Fausey N. R. (2015). Contributions of systematic tile drainage to
8 watershed-scale phosphorus transport. *Journal of Environmental Quality* **44**(2), 486-94.
- 9 Kirk D. W., Jia C. Q., Yan J. and Torrenueva A. L. (2003). Wastewater remediation using coal ash.
10 *Integrated Management of Hazardous Waste* **5**, 5-8.
- 11 Kumar P. S., Korving L., van Loosdrecht M. C. and Witkamp G.-J. (2019). Adsorption as a technology
12 to achieve ultra-low concentrations of phosphate: Research gaps and economic analysis.
13 *Water Research X* **4**, 100029.
- 14 Li D., Lv Y., Zeng H. and Zhang J. (2016). Enhanced biological phosphorus removal using granules in
15 continuous-flow reactor. *Chemical Engineering Journal* **298**, 107-16.
- 16 Liu J., Wan L., Zhang L. and Zhou Q. (2011). Effect of pH, ionic strength, and temperature on the
17 phosphate adsorption onto lanthanum-doped activated carbon fiber. *Journal of colloid and*
18 *Interface Science* **364**(2), 490-6.
- 19 Mezenner N. Y. and Bensmaili A. (2009). Kinetics and thermodynamic study of phosphate adsorption
20 on iron hydroxide-eggshell waste. *Chemical Engineering Journal* **147**(2-3), 87-96.
- 21 Omran I. I., Al-Saati N. H., Hashim K. S., Al-Saati Z. N., Patryk K., Khaddar R. A., Al-Jumeily D.,
22 Shaw A., Ruddock F. and Aljefery M. (2019). Assessment of heavy metal pollution in the
23 Great Al-Mussaib irrigation channel. *Desalination and Water Treatment* **168**, 165-74.
- 24 Pallant J. (2005). *SPSS SURVIVAL MANUAL*. Allen & Unwin, Australia.
- 25 Park H., Nguyen D. C. and Na C.-K. (2015). Phosphate removal from aqueous solutions using
26 (vinylbenzyl) trimethylammonium chloride grafted onto polyester fibers. *Water science and*
27 *technology* **71**(12), 1875-83.
- 28 Sellner B. (2016). *Evaluating steel byproducts and natural minerals for phosphate adsorption from*
29 *agricultural subsurface drainage*. MSc, Civil Engineering, South Dakota State University,
30 USA, USA.
- 31 Shubbar A. A., Jafer H., Dulaimi A., Hashim K., Atherton W. and Sadique M. (2018). The
32 development of a low carbon binder produced from the ternary blending of cement, ground
33 granulated blast furnace slag and high calcium fly ash: An experimental and statistical
34 approach. *Construction and building materials* **187**, 1051-60.
- 35 Tyagi S., Rawtani D., Khatri N. and Tharmavaram M. (2018). Strategies for nitrate removal from
36 aqueous environment using nanotechnology: a review. *Journal of Water Process Engineering*
37 **21**, 84-95.
- 38 Viswanadham B. V. S. (2016). Soil Mechanics. <http://textofvideo.nptel.iitm.ac.in/105101084/lec7.pdf>
39 (accessed 08/02/2016).
- 40 Weng L., Van Riemsdijk W. H. and Hiemstra T. (2012). Factors controlling phosphate interaction with
41 iron oxides. *Journal of Environmental Quality* **41**(3), 628-35.

- 1 Withers P. J., Neal C., Jarvie H. P. and Doody D. G. (2014). Agriculture and eutrophication: where do
2 we go from here? *Sustainability* **6**(9), 5853-75.
- 3 Xu X., Gao B., Wang W., Yue Q., Wang Y. and Ni S. (2009). Adsorption of phosphate from aqueous
4 solutions onto modified wheat residue: characteristics, kinetic and column studies. *Colloids*
5 *and Surfaces B: Biointerfaces* **70**(1), 46-52.
- 6 Yan L.-g., Xu Y.-y., Yu H.-q., Xin X.-d., Wei Q. and Du B. (2010). Adsorption of phosphate from
7 aqueous solution by hydroxy-aluminum, hydroxy-iron and hydroxy-iron–aluminum pillared
8 bentonites. *Journal of hazardous materials* **179**(1-3), 244-50.
- 9 Zalidis G., Stamatiadis S., Takavakoglou V., Eskridge K. and Misopolinos N. (2002). Impacts of
10 agricultural practices on soil and water quality in the Mediterranean region and proposed
11 assessment methodology. *Agriculture, Ecosystems & Environment* **88**(2), 137-46.
- 12 Zhang B. and Poon C. S. (2015). Use of furnace bottom ash for producing lightweight aggregate
13 concrete with thermal insulation properties. *Journal of Cleaner Production* **99**, 94-100.
- 14 Zhao B., Zhang Y., Dou X., Yuan H. and Yang M. (2015). Granular ferric hydroxide adsorbent for
15 phosphate removal: demonstration preparation and field study. *Water science and technology*
16 **72**(12), 2179-86.
- 17 Zhou H., Bhattarai R., Li Y., Li S. and Fan Y. (2019). Utilization of coal fly and bottom ash pellet for
18 phosphorus adsorption: Sustainable management and evaluation. *Resources, Conservation*
19 *and Recycling* **149**, 372-80.

20