



LJMU Research Online

Quraya, AB, Al-Ameeri, A, Hashim, R, Yeboah, D, Shubbar, AAF, AL-Hayawi, AY, Al-Jumeily, D and Mustafina, J

Experimental Investigations of Partial Replacement of OPC with PFA and GGBS in cement mortar

<http://researchonline.ljmu.ac.uk/id/eprint/14667/>

Article

Citation (please note it is advisable to refer to the publisher's version if you intend to cite from this work)

Quraya, AB, Al-Ameeri, A, Hashim, R, Yeboah, D, Shubbar, AAF, AL-Hayawi, AY, Al-Jumeily, D and Mustafina, J (2020) Experimental Investigations of Partial Replacement of OPC with PFA and GGBS in cement mortar. IOP Conference Series: Materials Science and Engineering. 1058 (1). ISSN 1757-

LJMU has developed [LJMU Research Online](http://researchonline.ljmu.ac.uk/) for users to access the research output of the University more effectively. Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Users may download and/or print one copy of any article(s) in LJMU Research Online to facilitate their private study or for non-commercial research. You may not engage in further distribution of the material or use it for any profit-making activities or any commercial gain.

The version presented here may differ from the published version or from the version of the record. Please see the repository URL above for details on accessing the published version and note that access may require a subscription.

For more information please contact researchonline@ljmu.ac.uk

<http://researchonline.ljmu.ac.uk/>

PAPER • OPEN ACCESS

Experimental Investigations of Partial Replacement of OPC with PFA and GGBS in cement mortar

To cite this article: Abdullah Bin Quraya *et al* 2021 *IOP Conf. Ser.: Mater. Sci. Eng.* **1058** 012004

View the [article online](#) for updates and enhancements.

Experimental Investigations of Partial Replacement of OPC with PFA and GGBS in cement mortar

Abdullah Bin Quraya^{1,*}, Abbas Al-Ameeri², Raad Hashim², David Yeboah¹, Ali Shubbar^{1,3}, Anas Y. AL-Hayawi⁴, Dhiya Al-Jumeily¹, Jamila Mustafina⁵

¹ Liverpool John Moores University, United Kingdom

² Faculty of Engineering, University of Babylon, Babylon, Iraq.

³ Department of Building and Construction Technical Engineering, College of Technical Engineering, the Islamic University, 54001 Najaf, Iraq.

⁴ Biology Department, College of education for pure sciences, Tikrit University, Iraq.

⁵ Kazan Federal University, Russia.

Email: A.M.BinQuraya@2017.ljmu.ac.uk

Abstract. Production of cement has been identified as a major source of carbon dioxide, particulates, and other gases, where it was reported that the production of one ton of OPC could produce one ton of CO₂. These gases and particulates exert significant effects on human health and the environment. Therefore, the supplementary cementitious materials (SCMs) are becoming sustainable concrete in comparison with ordinary Portland cement (OPC) by decreasing the consumption of cement and carbon dioxide emissions. This experimental study is to focus on the effect of partial replacement in cement by pulverized fly ash (PFA) and ground granulated blast furnace slag (GGBS). Four mixes were used with different values of PFA and GGBS and they tested at 1, 2, and 4 weeks. The compressive strength of these specimens was carried out by a compression test. The test results revealed that increasing the ratios of PFA and GGBS replacement results in a decrease in the compressive strength of specimens. The decrease in compressive strength of SCMs mortar ranged from 20 to 30%, and they could be an acceptable value.

1. Introduction

In today's world, concrete plays a vital role in the construction industry, and the most important ingredient of the concrete is ordinary Portland cement (OPC) [1, 2]. However, the production of cement has become a growing concern as a large amount of carbon dioxide (CO₂), particulates, and other gases are released into the atmosphere during this process [3-5]. For example, the available literature confirms that the cement industry contributes by about 6% to 8% of the total concentration of CO₂ in the atmosphere [6, 7]. In simple words, it is estimated that producing one ton of OPC could produce one ton of CO₂. These gases and particulates caused severe changes in the average weather temperature, and the climate in general, where it has been proved that the produced gases from the cement industry contribute to climate change and global warming. The latter phenomena threaten public health through maximizing water pollution [8-12], and the lack of rain in some parts of the world [13-16]. Moreover, the concrete plants produce large amounts of wastewaters that have a very high concentration of suspended particles and very high pH level (up to 11) and turbidity [17-19], which threaten the aquatic life in the receiving water bodies [19-21]. Therefore, the negative impacts of the cement and concrete industries on the public health and the environment, efficient management plans along with expressive wastewater treatments, such as filtration [22-26], combined methods [27-30], coagulation [31-40], and electro-chemical methods [41-46] and disposal options [47-49].

Recently, a number of researchers were directed to find alternative cementitious materials that replace a part of cement, such as fly ash (FA) and ground granulated blast furnace slag (GGBS) [50]. Using these mineral admixtures as a partial cement replacement could reduce costs, conserve energy, and minimize the emission of gases. Ground granulated blast furnace slag (GGBS) and Pulverised Fly Ash (PFA) are commonly used in partial replacement of OPC due to their pozzolanic properties. Thus, using these materials makes a significant contribution to the characteristics properties of the cement mortar [50, 51].

In this study, the pulverized fly ash (PFA) and ground granulated blast furnace slag (GGBS) were assessed with ordinary Portland cement (OPC). The main goal of this study is to examine the effects of using these materials on the compressive strength of the cement mortar at different curing ages (1, 2, and 4 weeks).

2. Experimental program

Many tests have been conducted to compare the compression strength of the cement mortar made by partial replacement of OPC with PFA and GGBS. Mix design and the percentages of PFA and GGBS that used in tests are disused later.

2.1. Materials

In this study, the PFA and GGBS were used as binder materials. Fly ashes, which is called pulverized fuel ash (PFA) in the UK, are by-products of the burning of pulverized coals in electricity generation plants. The carbon and volatile materials are burned off when the pulverized coals are burnt in the combustion chamber. Then some materials are fused to form the ash which is driven out of the boiler. This ash is collected by some filtration equipment, and after molten materials cool. This ash solidifies as sphere-shaped glassy particles known as Fly Ash that generally have an average size of 0.5-300 μm , which is slightly larger than the size of the particles of OPC. The ground granulated blast furnace slag (GGBS) is the waste of the iron and steel industries; this material has a glassy granular structure with large grain sizes. Thus, it is subjected, after the drying process, to a grinding process to minimize their sizes into fine powders. Normally, GGBS is used when there is a need to obtain a durable concrete structure with the OPC. In this study, the Ordinary Portland cement (OPC) was utilized as the basic binder due to its good adhesive characteristics that serve its bonding with other components of the mixture. The cement used in this work was examined according to BS-EN 196-2:2013. The physical and chemical properties of geopolymer binders are listed in Table 1. These properties of cement, PFA, and GGBS are fulfilled to BS-EN 197-1:2011, BS-EN 450-1:2012, and BS-EN 15167-1:2006, respectively. Local clean river sands were utilized as fine aggregates. (particle sizes < 5mm). The particle size distributions, and chlorides and sulphates contents were measured according to the BS-EN 12620:2002+A1:2008. Also, the portable water (free from organics) was used for mixtures as well as for the curing of samples.

Table 1. Properties of geopolymer binders.

Particulars (%)	PFA	GGBS
Chemical composition		
SiO ₂	65,6	30,61
Al ₂ O ₃	28,0	16,24
Fe ₂ O ₃	3,0	0,584
CaO	1,0	34,48
MgO	1,0	6,79
TiO ₂	0,5	0,0
SO ₃	0,2	1,85
Losses during ignition	0,29	2,1
Physical Properties		
Specific gravity	2,13	2,9
Fineness (m ² /kg)	360,0	400,0

2.2. Test methods

To measure the compressive strength of cement mortar, three cubes (100x100x100 mm) were cast and tested for each case. The considerable cases include testing the cubes by using only OPC, and then with the different replacement ratio of PFA and GGBS. All cubes were kept in appropriate condition and after 1 week of casting, they demolded and placed in water for curing. Later, the compressive strength was measured at the ages of 1, 2, and 4 weeks.

2.3. Mix Design

The mix design procedure adopted in the present work involves choosing the amount of cement, water, fine aggregate, and mineral admixture materials in a mortar mixture. The fine aggregate was chosen to fit the standard grading curves. The water to binder (cement+fly ash + GGBS) ratio is taken 0.4 for all the mixes. While the proportion of sand to binder was one part of cement to 2.5 parts of sand. The weight of each component/ingredients and the mix design proportion is listed in Table 2. It should be mentioned that the compression test applied to these specimens to exam the characteristics of cement mortar. Normally, cubes of 100x100x100 mm can be used to investigate the properties of cement mortar with PFA and GGBS. These samples were tested using a compression machine after 1, 2, and 4 weeks of curing. The testing load was applied gradually until the specimens fail. The compressive strength of samples can be computed by dividing the applied load on the area of the cube that is exposed to load (100*100 mm).

Table 2. Components of mix proportions

Cement (OPC)	(PFA)	(GGBS)
100 %	0 %	0 %
70 %	15 %	15 %
50 %	25 %	25 %
30 %	35 %	35%

3. Results

The results of the compressive strength tests of cement mortar with partial replacement of PFA and GGBS at various percentages at different curing periods are presented in Tables (1) and Figures 1 and 2.

Table 3. Compressive strengths at age 1, 2, and 4 weeks.

Test No.	OPC %	PFA %	GGBS %	Average of compressive strength (MPa) at		
				1 week	2 weeks	4 weeks
1	100	0	0	10.4	11.4	13.7
2	70	15	15	9.4	10.3	11.2
3	50	25	25	5.8	8.5	9.0
4	30	35	35	5.2	6.4	7.0

Key observations from these results are:

(i): It can be seen that using a partial replacement of PFA and GGBS in mixes results in a reduction in the compressive strengths of cementitious mortar. It could be noticed that mix 2 shows less decrease in the compressive strength when compared with those of 3 and 4. For example, at 1 week of curing, the reduction of compressive strength for the three mixes in comparison with the first mix was 10%, 44%, and 50 % respectively (Figure 2).

On the other hand, it can be noticed, for example, that using 50% a partial replacement material dropped the compressive strength of mortar by around half at 1 week, but this ratio decreased to be 20% at 28 curings. This means that PFA and GGBS are inactive material at an early age and they need time to interact with the components of a cement. To sum up, the partial replacement of PFA and GGBS can be done between 20 to 30% to get good strength and reduce environmental pollution. This can be attributed to the fact that the SCMs reduces the compressive strength of cementitious mortar which is a

significant factor in production gel (C-S-H) in mortar. Because of these react after hydration of cement and use the hydration products, $\text{Ca}(\text{OH})_2$ to active and start the hydration of PFA and GGBS.

(ii): The results exhibit higher compressive strength for samples are curing 4 weeks. This can be explained by the fact that the curing age affects gain and increase of C-S-H that leads to reduce the volume of internal voids or porosity in the structure of mortar that in turn affects the density of concrete and increase of compressive strength of these mixes. For example, the percentages increase in compressive strength for mix 4 at 2 and 4 weeks were 23% and 35% respectively compared with the same samples at 1 week.

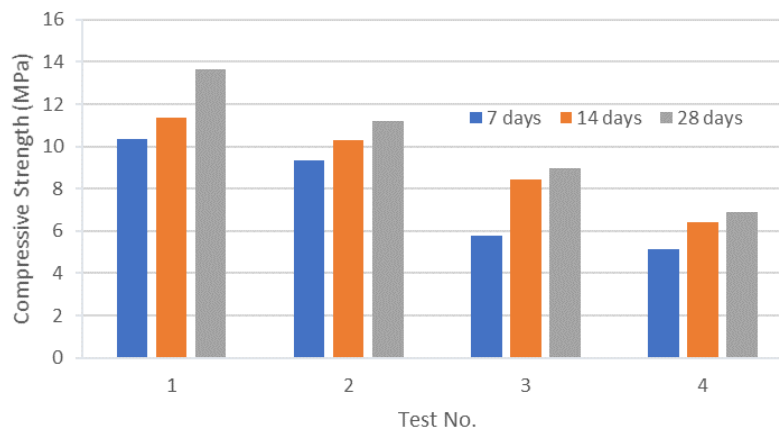


Figure 1. Compressive Strength for mixes at ages 1, 2, and 4 weeks.

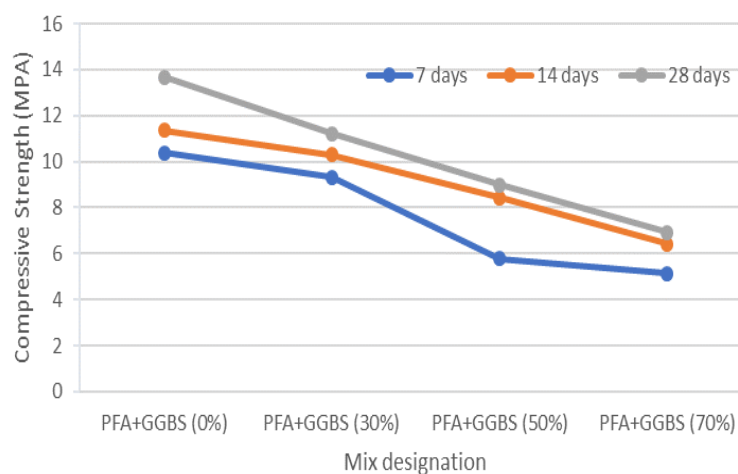


Figure 2. Effect of partial replacement of PFA and GGBS on compressive strength

The present work investigated the compressive for the concrete samples for 4 weeks, therefore more studies are required to investigate longer ages and compare the results with the traditional concrete samples of the same ages. Embedded sensors could be used for this purpose [52, 53], because of sensors shown good quality data in many fields, such as water quality [54] and communications [55].

4. Conclusions

Based on the results of this study, it can be drawn some points and as follows:

1. The partial replacement of PFA and GGBS of OPC in mortars decreases in compressive strength when an increase in percentage.
2. Increase the curing period is essential to obtain higher values of compressive strength when additional material is used in the mix.
3. Using 20 – 30 % as partial replacement of cement could be acceptable values, where increase this value leads to a drop in compressive strength of the concrete.

For future extension of this study more ages must be investigated because the present work investigated the compressive for the concrete samples for only 4 weeks. Embedded sensors could be used for this purpose because sensors have shown good quality data in many fields of civil and environmental engineering.

Acknowledgment

I wish to express my sincere thanks to all who helped me in doing this project work.

References

- [1] Shubbar A A, Jafer H, Dulaimi A, Hashim K, Atherton W and Sadique M 2018 The development of a low carbon binder produced from the ternary blending of cement, ground granulated blast furnace slag and high calcium fly ash: An experimental and statistical approach *Construction and Building Materials* **187** 1051-60.
- [2] Al-Jumeily D, Hashim K, Alkaddar R, Al-Tufaily M and Lunn J 2019 Sustainable and Environmental Friendly Ancient Reed Houses (Inspired by the Past to Motivate the Future) *11th International Conference on Developments in eSystems Engineering (DeSE)*
- [3] Kadhim A, Sadique M, Al-Mufti R and Hashim K 2020 Developing One-Part Alkali-Activated metakaolin/natural pozzolan Binders using Lime Waste as activation Agent *Advances in Cement Research* **32** 1-38.
- [4] Shubbar A A, Sadique M, Nasr M S, Al-Khafaji Z S and Hashim K S 2020 The impact of grinding time on properties of cement mortar incorporated high volume waste paper sludge ash *Karbala International Journal of Modern Science* **6** 1-23.
- [5] Grmasha R A, Al-sareji O J, Salman J M, Hashim K S and Jasim I A 2020 Polycyclic Aromatic Hydrocarbons (PAHs) in Urban Street Dust Within Three Land-Uses of Babylon Governorate, Iraq: Distribution, Sources, and Health Risk Assessment *Journal of King Saud University - Engineering Sciences* **33** 1-18.
- [6] Majdi H S, Shubbar A, Nasr M S, Al-Khafaji Z S, Jafer H, Abdulredha M, Masoodi Z A, Sadique M and Hashim K 2020 Experimental data on compressive strength and ultrasonic pulse velocity properties of sustainable mortar made with high content of GGBFS and CKD combinations *Data in Brief* **31** 105961-72.
- [7] Shubbar A A, Sadique M, Shanbara H K and Hashim K 2020 *The Development of a New Low Carbon Binder for Construction as an Alternative to Cement. In Advances in Sustainable Construction Materials and Geotechnical Engineering* (Berlin: Springer).
- [8] Zubaidi S L, Hashim K, Ethaib S, Al-Bdairi N S S, Al-Bugharbee H and Gharghan S K 2020 A novel methodology to predict monthly municipal water demand based on weather variables scenario *Journal of King Saud University-Engineering Sciences* **32** 1-18.
- [9] Zubaidi S L, Ortega-Martorell S, Al-Bugharbee H, Olier I, Hashim K S, Gharghan S K, Kot P and Al-Khaddar R 2020 Urban Water Demand Prediction for a City that Suffers from Climate Change and Population Growth: Gauteng Province case study *Water* **12** 1-18.
- [10] Zubaidi S L, Ortega-Martorell S, Kot P, Alkhaddar R M, Abdellatif M, Gharghan S K, Ahmed M S and Hashim K 2020 A Method for Predicting Long-Term Municipal Water Demands Under Climate Change *Water Resources Management* **34** 1265-79.
- [11] Zubaidi S L, Al-Bugharbee H, Muhsen Y R, Hashim K, Alkhaddar R M, Al-Jumeily D and Aljaaf A J 2019 The Prediction of Municipal Water Demand in Iraq: A Case Study of Baghdad Governorate *12th International Conference on Developments in eSystems Engineering (DeSE)*
- [12] Zubaidi S L, Kot P, Hashim K, Alkhaddar R, Abdellatif M and Muhsin Y R 2019 Using LARS-WG model for prediction of temperature in Columbia City, USA *IOP Conference Series: Materials Science and Engineering* 584.
- [13] Zanki A K, Mohammad F H, Hashim K S, Muradov M, Kot P, Kareem M M and Abdulhadi B 2020 Removal of organic matter from water using ultrasonic-assisted electrocoagulation method *IOP Conference Series: Materials Science and Engineering* 888.
- [14] Zubaidi S, Al-Bugharbee H, Ortega Martorell S, Gharghan S, Olier I, Hashim K, Al-Bdairi N and Kot P 2020 A Novel Methodology for Prediction Urban Water Demand by Wavelet Denoising and Adaptive Neuro-Fuzzy Inference System Approach *Water* **12** 1-17.

- [15] Zubaidi S L, Abdulkareem I H, Hashim K S, Al-Bugharbee H, Ridha H M, Gharghan S K, Al-Qaim F F, Muradov M, Kot P and Alkhaddar R 2020 Hybridised Artificial Neural Network model with Slime Mould Algorithm: A novel methodology for prediction urban stochastic water demand *Water* **12** 1-18.
- [16] Zubaidi S L, Al-Bugharbee H, Muhsin Y R, Hashim K and Alkhaddar R 2020 Forecasting of monthly stochastic signal of urban water demand: Baghdad as a case study *IOP Conference Series: Materials Science and Engineering* 888.
- [17] Alyafei A, AlKizwini R S, Hashim K S, Yeboah D, Gkantou M, Al Khaddar R, Al-Faluji D and Zubaidi S L 2020 Treatment of effluents of construction industry using a combined filtration-electrocoagulation method *IOP Conference Series: Materials Science and Engineering* 888.
- [18] Hassan Alnaimi I J I, Abuduljaleel Al-Janabi, Khalid Hashim, Michaela Gkantou, Salah L. Zubaidi, Patryk Kot, Magomed Muradov 2020 Ultrasonic-electrochemical treatment for effluents of concrete plants Ultrasonic-electrochemical treatment for effluents of concrete plants *IOP Conference Series Materials Science and Engineering* 888.
- [19] Hashim K S, Ewadh H M, Muhsin A A, Zubaidi S L, Kot P, Muradov M, Aljefery M and Al-Khaddar R 2020 Phosphate removal from water using bottom ash: Adsorption performance, coexisting anions and modelling studies *Water Science and Technology* **83** 1-17.
- [20] Alattabi A W, Harris C, Alkhaddar R, Alzeyadi A and Hashim K 2017 Treatment of Residential Complexes' Wastewater using Environmentally Friendly Technology *Procedia Engineering* **196** 792-9.
- [21] Alattabi A W, Harris C B, Alkhaddar R M, Hashim K S, Ortoneda-Pedrola M and Phipps D 2017 Improving sludge settleability by introducing an innovative, two-stage settling sequencing batch reactor *Journal of Water Process Engineering* **20** 207-16.
- [22] Abduraheem F S, Al-Khafaji Z S, Hashim K S, Muradov M, Kot P and Shubbar A A 2020 Natural filtration unit for removal of heavy metals from water *IOP Conference Series: Materials Science and Engineering* 888.
- [23] Alenazi M, Hashim K S, Hassan A A, Muradov M, Kot P and Abdulhadi B 2020 Turbidity removal using natural coagulants derived from the seeds of *strychnos potatorum*: statistical and experimental approach *IOP Conference Series: Materials Science and Engineering* 888.
- [24] Alenezi A K, Hasan H A, Hashim K S, Amoako-Attah J, Gkantou M, Muradov M, Kot P and Abdulhadi B 2020 Zeolite-assisted electrocoagulation for remediation of phosphate from calcium-phosphate solution *IOP Conference Series: Materials Science and Engineering* 888.
- [25] Hashim K, Kot P, Zubaid S, Alwash R, Al Khaddar R, Shaw A, Al-Jumeily D and Aljefery M 2020 Energy efficient electrocoagulation using baffle-plates electrodes for efficient *Escherichia Coli* removal from Wastewater *Journal of Water Process Engineering* **33** 101079-86.
- [26] Hashim K S, Idowu I A, Jasim N, Al Khaddar R, Shaw A, Phipps D, Kot P, Pedrola M O, Alattabi A W and Abdulredha M 2018 Removal of phosphate from River water using a new baffle plates electrochemical reactor *MethodsX* **5** 1413-8.
- [27] Hashim K S, Shaw A, Al Khaddar R, Ortoneda Pedrola M and Phipps D 2017 Defluoridation of drinking water using a new flow column-electrocoagulation reactor (FCER) - Experimental, statistical, and economic approach *Journal of Environmental Management* **197** 80-8.
- [28] Hashim K S, Shaw A, Al Khaddar R, Pedrola M O and Phipps D 2017 Iron removal, energy consumption and operating cost of electrocoagulation of drinking water using a new flow column reactor *Journal of Environmental Management* **189** 98-108.
- [29] Hashim K S, Shaw A, Al Khaddar R, Pedrola M O and Phipps D 2017 Energy efficient electrocoagulation using a new flow column reactor to remove nitrate from drinking water - Experimental, statistical, and economic approach *Journal of Environmental Management* **196** 224-33.
- [30] Hashim K S, Al-Saati N H, Hussein A H and Al-Saati Z N 2018 An investigation into the level of heavy metals leaching from canal-dredged sediment: a case study metals leaching from dredged sediment *First International Conference on Materials Engineering & Science*
- [31] Abdulla G, Kareem M M, Hashim K S, Muradov M, Kot P, Mubarak H A, Abdellatif M and Abdulhadi B 2020 Removal of iron from wastewater using a hybrid filter *IOP Conference Series: Materials Science and Engineering* 888.

- [32] Alhendal M, Nasir M J, Hashim K S, Amoako-Attah J, Al-Faluji D, Muradov M, Kot P and Abdulhadi B 2020 Cost-effective hybrid filter for remediation of water from fluoride *IOP Conference Series: Materials Science and Engineering* 888.
- [33] Al-Marri S, AlQuzweeni S S, Hashim K S, AlKhaddar R, Kot P, AlKizwini R S, Zubaidi S L and Al-Khafaji Z S 2020 Ultrasonic-Electrocoagulation method for nitrate removal from water *IOP Conference Series: Materials Science and Engineering* 888.
- [34] Hashim K S, Ali S S M, AlRifaie J K, Kot P, Shaw A, Al Khaddar R, Idowu I and Gkantou M 2020 Escherichia coli inactivation using a hybrid ultrasonic–electrocoagulation reactor *Chemosphere* **247** 125868-75.
- [35] Abdulhadi B A, Kot P, Hashim K S, Shaw A and Khaddar R A 2019 Influence of current density and electrodes spacing on reactive red 120 dye removal from dyed water using electrocoagulation/electroflotation (EC/EF) process *First International Conference on Civil and Environmental Engineering Technologies (ICCEET)* 584.
- [36] Hashim K S, Al-Saati N H, Alquzweeni S S, Zubaidi S L, Kot P, Kraidi L, Hussein A H, Alkhaddar R, Shaw A and Alwash R 2019 Decolourization of dye solutions by electrocoagulation: an investigation of the effect of operational parameters *First International Conference on Civil and Environmental Engineering Technologies (ICCEET)* 584.
- [37] Hashim K S, Hussein A H, Zubaidi S L, Kot P, Kraidi L, Alkhaddar R, Shaw A and Alwash R 2019 Effect of initial pH value on the removal of reactive black dye from water by electrocoagulation (EC) method *2nd International Scientific Conference*
- [38] Hashim K S, Khaddar R A, Jasim N, Shaw A, Phipps D, Kot P, Pedrola M O, Alattabi A W, Abdulredha M and Alawsh R 2019 Electrocoagulation as a green technology for phosphate removal from River water *Separation and Purification Technology* **210** 135-44.
- [39] Al-Saati N H, Hussein T K, Abbas M H, Hashim K, Al-Saati Z N, Kot P, Sadique M, Aljefery M H and Carnacina I 2019 Statistical modelling of turbidity removal applied to non-toxic natural coagulants in water treatment: a case study *Desalination and Water Treatment* **150** 406-12.
- [40] Omran I I, Al-Saati N H, Hashim K S, Al-Saati Z N, Patryk K, Khaddar R A, Al-Jumeily D, Shaw A, Ruddock F and Aljefery M 2019 Assessment of heavy metal pollution in the Great Al-Mussaib irrigation channel *Desalination and Water Treatment* **168** 165-74.
- [41] Aqeel K, Mubarak H A, Amoako-Attah J, Abdul-Rahaim L A, Al Khaddar R, Abdellatif M, Al-Janabi A and Hashim K S 2020 Electrochemical removal of brilliant green dye from wastewater *IOP Conference Series: Materials Science and Engineering* 888.
- [42] Mohammed A-H, Hussein A H, Yeboah D, Al Khaddar R, Abdulhadi B, Shubbar A A and Hashim K S 2020 Electrochemical removal of nitrate from wastewater *IOP Conference Series: Materials Science and Engineering* 888.
- [43] Abdulhadi B, Kot P, Hashim K, Shaw A, Muradov M and Al-Khaddar R 2021 Continuous-flow electrocoagulation (EC) process for iron removal from water: Experimental, statistical and economic study *Science of The Total Environment* **756** 1-16.
- [44] Hashim K S, Shaw A, AlKhaddar R, Kot P and Al-Shamma'a A 2021 Water purification from metal ions in the presence of organic matter using electromagnetic radiation-assisted treatment *Journal of Cleaner Production* **280**
- [45] Hashim K S, AlKhaddar R, Shaw A, Kot P, Al-Jumeily D, Alwash R and Aljefery M H 2020 *Electrocoagulation as an eco-friendly River water treatment method. In Advances in Water Resources Engineering and Management* (Berline: Springer).
- [46] Emamjomeh M M, Mousazadeh M, Mokhtari N, Jamali H A, Makkiabadi M, Naghdali Z, Hashim K S and Ghanbari R 2020 Simultaneous removal of phenol and linear alkylbenzene sulfonate from automotive service station wastewater: Optimization of coupled electrochemical and physical processes *Separation Science and Technology* **55** 3184-94.
- [47] Abdulredha M, Rafid A, Jordan D and Hashim K 2017 The development of a waste management system in Kerbala during major pilgrimage events: determination of solid waste composition *Procedia Engineering* **196** 779-84.
- [48] Idowu I A, Atherton W, Hashim K, Kot P, Alkhaddar R, Alo B I and Shaw A 2019 An analyses of the status of landfill classification systems in developing countries: Sub Saharan Africa landfill experiences *Waste Management* **87** 761-71.

- [49] Abdulredha M, Al Khaddar R, Jordan D, Kot P, Abdulridha A and Hashim K 2018 Estimating solid waste generation by hospitality industry during major festivals: A quantification model based on multiple regression *Waste Management* **77** 388-400.
- [50] Shubbar A A, Al-Shaer A, AlKizwini R S, Hashim K, Hawesah H A and Sadique M 2019 Investigating the influence of cement replacement by high volume of GGBS and PFA on the mechanical performance of cement mortar *First International Conference on Civil and Environmental Engineering Technologies (ICCEET)* 584.
- [51] Kadhim A, Sadique M, Al-Mufti R and Hashim K 2020 Long-term performance of novel high-calcium one-part alkali-activated cement developed from thermally activated lime kiln dust *Journal of Building Engineering* **32** 1-17.
- [52] Gkantou M, Muradov M, Kamaris G S, Hashim K, Atherton W and Kot P 2019 Novel Electromagnetic Sensors Embedded in Reinforced Concrete Beams for Crack Detection *Sensors* **19** 5175-89.
- [53] Teng K H, Kot P, Muradov M, Shaw A, Hashim K, Gkantou M and Al-Shamma'a A 2019 Embedded Smart Antenna for Non-Destructive Testing and Evaluation (NDT&E) of Moisture Content and Deterioration in Concrete *Sensors* **19** 547-59.
- [54] Ryecroft S P, shaw A, Fergus P, Kot P, Hashim K and Conway L 2019 A Novel Gesomin Detection Method Based on Microwave Spectroscopy *12th International Conference on Developments in eSystems Engineering (DeSE)*
- [55] Ryecroft S, Shaw A, Fergus P, Kot P, Hashim K, Moody A and Conway L 2019 A First Implementation of Underwater Communications in Raw Water Using the 433 MHz Frequency Combined with a Bowtie Antenna *Sensors* **19** 1813-23.