



LJMU Research Online

Al-Mamoori, SF, Shubbar, AAF, Al-Khafaji, ZS, Nasr, MS, Alkhayyat, A, Al-Rifaie, A, Latif Al-Mufti, RA, Sadique, MM and Hashim, KS

Production of Ternary Blend Binder as an Alternative to Portland Cement

<http://researchonline.ljmu.ac.uk/id/eprint/14686/>

Article

Citation (please note it is advisable to refer to the publisher's version if you intend to cite from this work)

Al-Mamoori, SF, Shubbar, AAF, Al-Khafaji, ZS, Nasr, MS, Alkhayyat, A, Al-Rifaie, A, Latif Al-Mufti, RA, Sadique, MM and Hashim, KS (2021) Production of Ternary Blend Binder as an Alternative to Portland Cement. IOP Conference Series: Materials Science and Engineering. 1090 (1). ISSN 1757-

LJMU has developed **LJMU Research Online** for users to access the research output of the University more effectively. Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Users may download and/or print one copy of any article(s) in LJMU Research Online to facilitate their private study or for non-commercial research. You may not engage in further distribution of the material or use it for any profit-making activities or any commercial gain.

The version presented here may differ from the published version or from the version of the record. Please see the repository URL above for details on accessing the published version and note that access may require a subscription.

For more information please contact researchonline@ljmu.ac.uk

<http://researchonline.ljmu.ac.uk/>

PAPER • OPEN ACCESS

Production of Ternary Blend Binder as an Alternative to Portland Cement

To cite this article: Shahad F. Al-Mamoori *et al* 2021 *IOP Conf. Ser.: Mater. Sci. Eng.* **1090** 012069

View the [article online](#) for updates and enhancements.



240th ECS Meeting ORLANDO, FL

Orange County Convention Center Oct 10-14, 2021



Abstract submission due: April 9

SUBMIT NOW

Production of Ternary Blend Binder as an Alternative to Portland Cement

Shahad F. Al-Mamoori ¹, Ali A. Shubbar ^{2,*}, Zainab S. Al-Khafaji ³, Mohammed Salah Nasr ⁴, Ahmed Alkhayyat ⁵, Ali Al-Rifaie ⁶, Rafal Latif Al-Mufti ², Monower Sadique ² and Khalid Hashim ²

¹ Department of Civil Engineering, College of Engineering, University of Babylon, Iraq

² Department of Civil Engineering, Liverpool John Moores University, UK.

³ Al-Furatt Al-Awsat Distribution Foundation \ Ministry of Oil \ Babylon, Iraq.

⁴ Babylon Technical Institute, Al-Furat Al-Awsat Technical University, 51015 Babylon, Iraq.

⁵ Department of Building and Construction Technical Engineering, College of Technical Engineering, the Islamic University, 54001 Najaf, Iraq.

⁶ College of Engineering, Al-Muthanna University, Samawah, 66001, Iraq.

* Corresponding author: alishubbar993@gmail.com , A.A.Shubbar@2014.ljmu.ac.uk

Abstract. Environmental pollution and the relatively high cost of waste disposal have been a major focus for scientists around the world, leading researchers to find a solution to reuse waste materials in different applications. Additionally, landfills are considered one of the biggest crisis facing the Iraqi government. Therefore, this study aims to present a new ternary mixture that consists of OPC in addition to Pulverized Fuel Ash (PFA), Ground Granulated Blast Furnace Slag (GGBS) by utilizing it as a partial substitution of cement. A new ternary mortar mixtures containing four substitution levels of cement with GGBS and PFA (0%, 30 %, 50% and 70% by weight) were carried out. The Ultrasonic Pulse Velocity (UPV) and compressive strength tests were adopted to show the influence of GGBS and PFA on mechanical features of cement mortar. Findings indicated that, the compressive strength values were reduced with increasing the GGBS and PFA proportions at all curing ages. For 70% replacement, the compressive strength values were the lowest values comparison with that for control specimens. In contrast, the GGBS and PFA had a negative and positive impacts on the UPV of mortar depending on the substitution ratio. At 30 % substitution levels, the velocity value was enhanced, while other substitution ratios affected negatively on the UPV values.

1. Introduction

The consequences of greenhouse gas emissions have been the concern of governments, scientists and companies due to its direct influence to global warming. Rates of carbon dioxide (CO₂) emissions are still rising up rapidly and the fear of irreversible changes is looming over these parties [1]. Thus, for the environment to be maintained, carbon dioxide emissions should be minimized [2]. One of the contributors to such phenomena is the cement industry [3–12]. In general, the percentage of 5-8% of total CO₂ produced by the man-kind [12–22]. While on the other hand the construction industry is showing a rapid growth which directly influence the demand of production of Portland cement as the cementitious material is an essential substance for concrete structures [23–25]. The research on studying Supplementary Cementitious Materials (SCM) that would aid the parties concerned to



decrease the negative influence of the production of Portland cement on cost and environment has been continuously encouraged and growing to conduct studies [26]. It was found that multiple industries generate waste materials that could be turned to by-products and used as SCMs by cement companies, industries such as the agriculture, steel and the coal industries could produce substances like rice husk ash (RHA), GGBS, and PFA [27,28]. Literature has showed lack of studies conducted on the influences of utilizing ternary blends that contains both GGBS and PFA in the mix with Ordinary Portland Cement [28].

Ground granulated blast-furnace slag (GGBS) is an extracted by-product from the steel factories or plants, specifically from the blast furnaces that are utilized to produce iron [29]. The formation of GGBS takes place once the blast furnace slag goes through rapid quenching which would eventually turn into glassy calcium-magnesium aluminosilicate granules. These granules can be later grinded to a certain degree of fine powder that would be optimum for use based on the requirements of usage [23,28]. GGBS contains two phases, the glassy phase which is responsible of the cementitious features within the material and the crystalline phase which allows the hydration of the material once its exposed to moisture in the mix with cement [30]. The usage of GGBS as a substitution of cement in partial percentages has yielded improved durability of specimens as higher strength levels has been recorded in the later ages and increased persistence to environmental abrasive wearing conditions [29].

PFA also alternatively called Fly ash (FA), is another supplementary cementitious material extracted from the coal industry. Pulverized coal once combusted in burning power plant would release residue, subsequently electrostatic or mechanical precipitators are used to capture the residue that flies out among the flue gas stream during the burning process [25]. PFA acts as a pozzolanic material due to its chemical features composition. This allows PFA to be used as a substitution of cement partially in concrete structures [31]. Studies have showed that the usage of PFA in a mix as a substitution of cement outcomes into lower hydration heat which was advantageous for dams construction [25], reduction of permeability in concrete that would protect the concrete from abrasive conditions therefore the durability is improved, and increased workability [31].

The shift for more eco-friendly/durable mixtures and the availability of pozzolanic admixtures has driven experiments and studies for binary and ternary blends for cement replacement. One of these ternary blends is the mixture of GGBS and PFA, this is due to the registered promising and improving mechanical and chemical features of the concrete mix after the inclusion of these materials together and separately [1]. After reviewing the literature, it was found that there are multiple studies on the influence of GGBS and PFA on cement binder, however, the majority of the studies experimented the influence of these materials separately. Kamau et al. [32] conducted a substitution experiment of cement with ternary blends using both GGBS and PFA in the mix and investigated the influence on the strength of specimens. The percentages of substitution were 0%, 5%, 7.5%, 10%, 15%, 20%, 25%, and 30%. It was concluded that both materials complement each other performance in the blend. The using of GGBS increased the strength of PFA, and the workability of GGBS enhanced by PFA. The compressive strength of samples showed an advantage over the binary and 0% substitution in lower levels of substitution and otherwise in higher level of substitution samples. More limitations were recorded as well, as the density of binary and 0% substitution samples were better than of the ternary blend. Tensile strength recorded lower levels as well than binary mixes. A following up study by the same author, Kamau and Ahmed [33] investigated the use of ternary blends over the individual binary mixes in challenging environments that would hinder the durability of concrete. The author found in $MgSO_4$ environments, the use of GGBS and PFA as ternary blends has an advantage when the substitution of cement is 30%. Higher levels of substitution showed preservation in both Na_2SO_4 and $MgSO_4$ environments. Sern et al. [1] did a further study on ternary blend with a goal of observing the influence of using more waste materials in the mix of the binder.

2. Work Methodology

2.1. Materials

2.1.1. *Binders.* PFA, GGBS, and Portland Cement (PC) were the components utilized in this inquiry. The cement is PC kind CEM-II / A / LL 32.5-N. Hanson Heidelberg Cement Group supplied GGBS whereas CEMEX ltd Corporation, Warwickshire, United Kingdom provided PFA and PC.

An Energy Dispersive X-ray Florescence Spectrometer (EDXRF) model Shimadzu EDX-720 evaluated the fundamental structure of PFA, GGBS and PC. The chemical compositions of the PFA, GGBS and PC are shown in Table 1.

Table 1. Chemical analysing of PFA, GGBS and PC.

Item	PC	GGBS	PFA
CaO	6521x10 ⁻²	4251x10 ⁻²	481x10 ⁻²
SiO ₂	2456x10 ⁻²	4106x10 ⁻²	5883x10 ⁻²
Al ₂ O ₃	170x10 ⁻²	512x10 ⁻²	1883x10 ⁻²
Fe ₂ O ₃	164x10 ⁻²	-	54x10 ⁻²
MgO	130x10 ⁻²	425x10 ⁻²	386x10 ⁻²
Na ₂ O	134x10 ⁻²	309x10 ⁻²	117x10 ⁻²
K ₂ O	82x10 ⁻²	69x10 ⁻²	204x10 ⁻²
SO ₃	262x10 ⁻²	127x10 ⁻²	106x10 ⁻²
TiO ₂	-	98x10 ⁻²	119x10 ⁻²
LOI	28x10 ⁻²	37x10 ⁻²	267x10 ⁻²
pH	1273x10 ⁻²	1102x10 ⁻²	1068x10 ⁻²
Specific Gravity	294x10 ⁻²	290x10 ⁻²	249x10 ⁻²

2.1.2. *Mixing Water.* Standard potable water (from tap) has been utilized for sample mixing.

2.1.3. *Aggregates.* Coarse and Fine aggregate depending on (BS 882: 1992) has been utilized in this project, obtainable in the "Liverpool" zone. The sieving test analysing is placed in Table (2).

Table 2. The sieve analysis of aggregates

Sieve Size (mm)	% Passing on every Sieve				
	(O/A) Limits	% Passing of the Specimen	Additional Limits		
			C	M	F
4.76	100	95	-	-	-
2.36	89-100	81.2	-	-	-
1.18	60-100	67.2	60-100	65-100	80-100
0.6	30-100	47.9	30-90	45-100	70-100
0.3	15-100	20.8	15-54	25-80	55-100
0.15	5-70	6.6	5-40	5-48	5-70

Coarse= C, Medium=M, Fine=F

2.2. Mix Proportions

The cement pastes, mortars and concrete mixes were prepared maintaining the levels of substitution of (GGBS +PFA) of (0, 30, 50, 70) % by weight of cement. A reference cement paste, mortar and concrete mix were also prepared for comparison. The blends were used to identified the optimum substitution ratios of (GGBS +PFA) as a ternary blending binder. Table 3 demonstrated the mix ratios utilized in this project. The sand/binder proportion (S/B) and water/binder (W/B) were, 2.5 and 0.4, respectively.

Table 3. Mix Design

Mix ID	OPC %	PFA %	GGBS %	S/B	W/B
RF	100	0	0	2.5	0.4
M1	70	15	15	2.5	0.4
M2	50	25	25	2.5	0.4
M3	30	35	35	2.5	0.4

2.3 Testes

- 1) Depending on BS EN 196-1, the test of compressive strength for all the mix has been performed (Two samples with sizes of 4x4x16 cm were generated at every curing period for each mixing ratio. Three points of loading of the prism samples split each sample into two sections and the average of 4 parts have been taken to indicate the final magnitudes of compressive strength).
- 2) The tests of UPV for all selected mix have been performed depending on BS 1881-203. (Three specimens with dimensions of 100x100x100 mm have been produced for each blending proportion at every period of curing).

3. Results and discussion

3.1 Compressive strength findings

The findings of the compressive strength for different blends are demonstrated in Figure 1. It could be realized from Figure 1 that extending the age of curing for different blends led to enhance the compressive strength performance of mortars. As shown in Figure 1, the compressive strength of mortar decreased with increasing the levels of substitution of OPC by GGBS and PFA at different curing periods.

At the age of 7 days, the substitution of OPC by 30% GGBS+PFA, 50% GGBS+PFA and 70% GGBS+PFA led to reduce the compressive strength by about 31%, 54% and 64%, respectively relative to the control blend (RF). Moving to the age of 14 days, the reduction in the compressive strength for the blend M1 was lower than that at the age of 7 days. This could be due to the low reactivity of GGBS and PFA at early ages that improves with extending the age of curing [5–7,17]. On the other hand, the mixes M3 and M2 demonstrated similar performance to that at the age of 7 days. After 28 days of curing, the mix M1 demonstrated about 74% of the compressive strength of the RF, while the mixes M3 and M2 demonstrated only about 48% and 39% of the compressive strength of the RF sample.

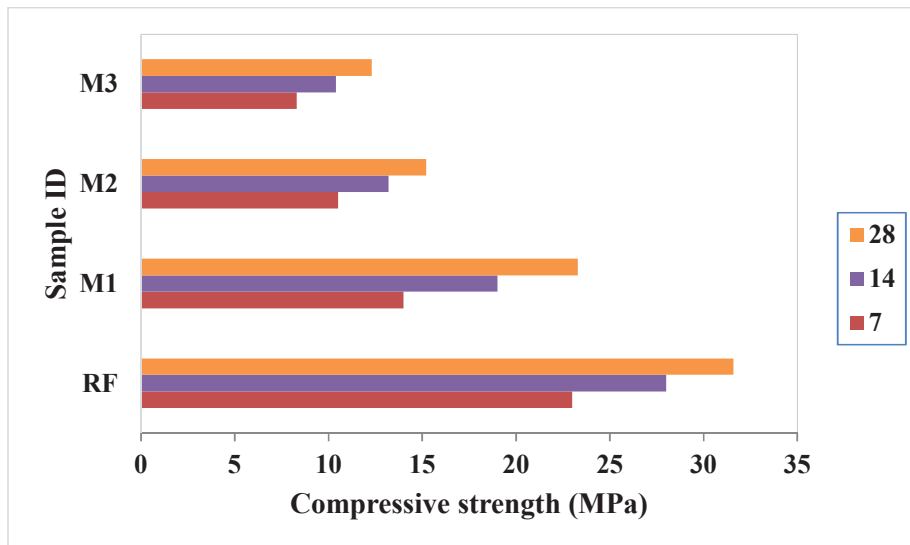


Figure 1. Compressive strength findings

3.2 UPV findings

The findings of the UPV test for different blends and for different periods of curing are presented in Figure 2. Figure 2 clearly demonstrates that extending the curing period for different mixtures led in improving the UPV values for all blends. The findings shows that extending the curing age for all mixtures helped in improving the UPV values of all blends. After 7 days of curing, the mixture M1 indicated an improvement in the UPV value relative to the RF mixture by about 0.3 %, while the mixtures M2 and M3 demonstrated a reduction in the UPV by nearly 9% and 20%, respectively. At the 14 curing days, the mixture M1 demonstrated similar finding to that of 7 days, while the UPV values of M2 and M3 improved by 8% and 10%, respectively. The findings of the UPV test after 28 days of curing indicated improvement in the UPV value for mixture M1 relative to RF by approximately 1%.

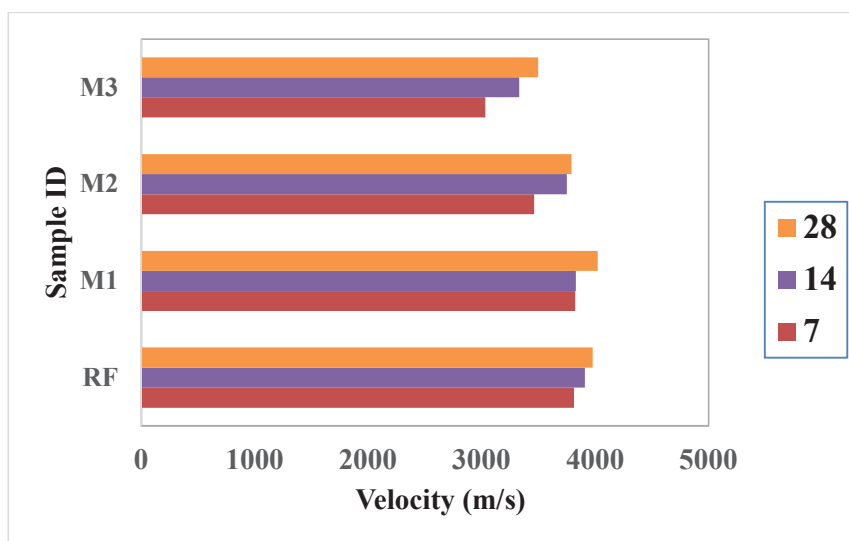


Figure 2. UPV findings.

4. Conclusion

The main goal of this investigation is to explore the features of cement mortar incorporated various percentages of PFA and GGBS. Depending on the obtained outcome, the next conclusions were collected.

- Extending the age of curing for all mixtures led to improve the UPV and compressive strength performances.
- The magnitudes of compressive strength of all the ternary mixtures were lesser than that of the RF at all ages.
- At all ages, the mixture M1 indicated better UPV values relative to the RF mixture.
- Accumulative the PFA and GGBS amount led to reduce the compressive strength at all ages.
- The mixture M2 showed comparable UPV value relative to the RF mixture after 28 days of curing.

Authors recommended utilizing other waste or by-products materials, for example stainless steel powder, silica fume, paper waste, crude oil wastes, agricultural waste [34–54], industrial wastes [55–57], municipal solid wastes [58] as well as water and wastewater planes waste [59–62] to improve the produced mortar. Utilisation of such materials in reinforced concrete beams is also considered as worthy issue [63].

References

- [1] Sern L J, Cheah C B and Ramli M B 2019 The setting behavior , mechanical properties and drying shrinkage of ternary blended concrete containing granite quarry dust and processed steel slag aggregate *Constr. Build. Mater.* **215** 447–61
- [2] Alsalmán A, Assi L N, Ghotbi S, Ghahari S and Shubbar A 2020 Users, Planners, and Governments Perspectives: A Public Survey on Autonomous Vehicles Future Advancements *Transp. Eng.*
- [3] Jafer H, Jawad I, Majeed Z and Shubbar A 2021 The development of an ecofriendly binder containing high volume of cement replacement by incorporating two by-product materials for the use in soil stabilization *Sci. Rev. Eng. Environ. Sci.* **30**
- [4] Nasr M S, Hasan Z A and Abed M K 2019 Mechanical Properties of Cement Mortar Made with Black Tea Waste Ash as a Partial Replacement of Cement *Eng. Technol. J.* **37, Part C** 45–9
- [5] Shubbar A A, Al-Shaer A, AlKizwini R S, Hashim K, Al Hawesah H and Sadique M 2019 Investigating the influence of cement replacement by high volume of GGBS and PFA on the mechanical performance of cement mortar *IOP Conference Series: Materials Science and Engineering* vol 584 (IOP Publishing) p 12022
- [6] Shubbar A A, Jafer H, Dulaimi A, Hashim K, Atherton W and Sadique M 2018 The development of a low carbon binder produced from the ternary blending of cement, ground granulated blast furnace slag and high calcium fly ash: an experimental and statistical approach *Constr. Build. Mater.* **187** 1051–60
- [7] Shubbar A A F, Jafer H M, Dulaimi A F D, Atherton W and Al-Rifaie A 2017 The Development of a Low Carbon Cementitious Material Produced from Cement, Ground Granulated Blast Furnace Slag and High Calcium Fly Ash *Int. J. Civil, Environ. Struct. Constr. Archit. Eng.* **11** 905–8
- [8] Nasr M S, Shubbar A A, Abed Z-A R and Ibrahim M S 2020 Properties of eco-friendly cement mortar contained recycled materials from different sources *J. Build. Eng.* **31** 101444
- [9] Shubbar A A, Al-Jumeily D, Aljaaf A J, Alyafei M, Sadique M and Mustafina J 2019 Investigating the Mechanical and Durability Performance of Cement Mortar Incorporated Modified Fly Ash and Ground Granulated Blast Furnace Slag as Cement Replacement Materials *2019 12th International Conference on Developments in eSystems Engineering (DeSE) (IEEE)* pp 434–9
- [10] Nasr M S, Hasan Z A, Abed M K, Dhahir M K, Najim W N, Shubbar A A and Dhahir H Z

- 2021 Utilization of High Volume Fraction of Binary Combinations of Supplementary Cementitious Materials in the Production of Reactive Powder Concrete *Period. Polytech. Civ. Eng.* **65** 335–43
- [11] Obaid M K, Nasr M S, Ali I M, Shubbar A A and Hashim K S 2021 Performance of Green Mortar Made from Locally Available Waste Tiles and Silica Fume *J. Eng. Sci. Technol. Technol.* **16**
- [12] Nasr M S, Ali I M, Hussein A M, Shubbar A A, Kareem Q T and AbdulAmeer A T 2020 Utilization of locally produced waste in the production of sustainable mortar *Case Stud. Constr. Mater.* **13** e00464
- [13] Hasan Z A, Nasr M S and Abed M K 2019 Combined Effect of Silica Fume, and Glass and Ceramic Waste on Properties of High Strength Mortar Reinforced With Hybrid Fibers *Int. Rev. Civ. Eng.* **10** 267–73
- [14] Hasan Z A, Nasr M S and Abed M K 2021 Properties of reactive powder concrete containing different combinations of fly ash and metakaolin *Mater. Today Proc.* **34**
- [15] Kubba H Z, Nasr M S, Al-Abdaly N M, Dhahir M K and Najim W N 2020 Influence of Incinerated and Non-Incinerated waste paper on Properties of Cement Mortar *IOP Conference Series: Materials Science and Engineering* vol 671 (IOP Publishing) p 12113
- [16] Shubbar A A, Sadique M, Kot P and Atherton W 2019 Future of clay-based construction materials—A review *Constr. Build. Mater.* **210** 172–87
- [17] Shubbar A A, Sadique M, Shanbara H K and Hashim K 2020 The Development of a New Low Carbon Binder for Construction as an Alternative to Cement *Advances in Sustainable Construction Materials and Geotechnical Engineering* (Springer) pp 205–13
- [18] Zainab S A K, Zainab A M, Jafer H, Dulaimi A F and Atherton W 2018 The effect of using fluid catalytic cracking catalyst residue (FC3R) as a cement replacement in soft soil stabilisation" *Int. J. Civ. Eng. Technol.* **9** 522–33
- [19] Nasr M S, Hussain T H and Najim W N 2018 Properties of Cement Mortar Containing Biomass Bottom Ash and Sanitary Ceramic Wastes as a Partial Replacement of Cement *Int. J. Civ. Eng. Technol.* **9** 153–65
- [20] Hussain A J and Al-Khafaji Z S 2020 The fields of applying the recycled and used oils by the internal combustion engines for purposes of protecting the environment against pollutions *J. Adv. Res. Dyn. Control Syst.* **12** 698–706
- [21] Shubbar A A, Sadique M, Nasr M S, Al-Khafaji Z S and Hashim K S 2020 The impact of grinding time on properties of cement mortar incorporated high volume waste paper sludge ash *Karbala Int. J. Mod. Sci.* **6** 396–403
- [22] Shubbar A A, Jafer H, Abdulredha M, Al-Khafaji Z S, Nasr M S, Al Masoodi Z and Sadique M 2020 Properties of cement mortar incorporated high volume fraction of GGBFS and CKD from 1 day to 550 days *J. Build. Eng.* **30** 101327
- [23] Deepa P R and Anup J 2016 Experimental Study on the Effect of Recycled Aggregate and GGBS on Flexural Behaviour of Reinforced Concrete Beam *Appl. Mech. Mater.* **857** 101–6
- [24] Srinivasa A S 2019 Experimental investigation of Mechanical properties of Geo polymer concrete with GGBS and Hybrid Fibers Experimental investigation of Mechanical properties of Geo polymer concrete with GGBS and Hybrid Fibers
- [25] Zhou X, Slater J R, Wavell S E, Oladiran O, Maruyama I, Zhou X M, Slater J R, Wavell S E and Oladiran O 2012 Effects of PFA and GGBS on Early-Ages Engineering Properties of Portland Cement Systems Effects of PFA and GGBS on Early-Ages Engineering Properties of Portland Cement Systems **10** 1–13
- [26] Kupwade-patil K, Wolf C De, Chin S and Ochsendorf J 2018 Impact of Embodied Energy on materials / buildings with partial replacement of ordinary Portland Cement (OPC) by natural Pozzolanitic Volcanic Ash *J. Clean. Prod.* **177** 547–54
- [27] Sakir S, Raman S N and Kaish A B M A 2020 Utilization of By-Products and Wastes as Supplementary Cementitious Materials in Structural Mortar for Sustainable Construction

Sustainability **12**

- [28] Chee C, Kok C, Ramli M and Gin L 2016 The engineering properties and microstructure development of cement mortar containing high volume of inter-grinded GGBS and PFA cured at ambient temperature *Constr. Build. Mater.* **122** 683–93
- [29] Qiang W and Dengquan W 2016 Contributions of fly ash and ground granulated blast-furnace slag to the early hydration heat of composite binder at different curing temperatures **28**
- [30] Hawileh R A, Abdalla J A, Fardmanesh F, Shahsana P and Khalili A 2017 Performance of reinforced concrete beams cast with different percentages of GGBS replacement to cement *Arch. Civ. Mech. Eng.* **17** 511–9
- [31] Duraman S B, Hakim F and Omar H 2019 Durability of pulverised fuel ash (PFA) concrete exposed to acidic and alkali conditions **5015**
- [32] Kamau J, Ahmed A, Hirst P and Kangwa J 2017 Performance of Class F Pulverised Fuel Ash and Ground Granulated Blast Furnace Slag in Ternary Concrete Mixes **2** 36–41
- [33] Kamau J and Ahmed A 2017 Performance of Ternary Class F Pulverised Fuel Ash and Ground Granulated Blast Furnace Slag Concrete in Sulfate Solutions 7–13
- [34] Majidi H S, Shubbar A A, Nasr M S, Al-Khafaji Z S, Jafer H, Abdulredha M, Masoodi Z Al, Sadique M and Hashim K 2020 Experimental data on compressive strength and ultrasonic pulse velocity properties of sustainable mortar made with high content of GGBFS and CKD combinations *Data Br.* **31** 105961
- [35] Al Hawesah H, Shubbar A and Al Mufti R L 2018 Non-destructive assessment of early age mortar containing stainless steel powder *Proceedings of the LJMU 17th Annual International Conference on: Asphalt, Pavement Engineering and Infrastructure* (Liverpool, UK: LIVERPOOL CENTRE FOR MATERIALS TECHNOLOGY)
- [36] Shanbara H K, Ruddock F and Atherton W 2017 Improving the Mechanical Properties of Cold Mix Asphalt Mixtures Reinforced by Natural and Synthetic Fibers *International Conference on Highway Pavements & airfield Technology* pp 102–11
- [37] Ali I M, Naje A S and Nasr M S 2020 Eco-Friendly Chopped Tire Rubber as Reinforcements in Fly Ash Based Geopolymer Concrete *Glob. NEST J.* **22** 342–7
- [38] Al-Salim N H A, Hassan R F and Jaber M H 2018 Compression Zone Rehabilitation of Damaged RC Beams Using Poleyster Glue Line *J. Eng. Appl. Sci.* **13** 1195–200
- [39] Hassan R F, Jaber M H, Al-Salim N H and Hussein H H 2020 Experimental research on torsional strength of synthetic/steel fiber-reinforced hollow concrete beam *Eng. Struct.* **220** 110948
- [40] Jaber M H, Al-Salim N H A and Hassan R F 2018 flexural behavior of hollow rectangular steel (HRS) section beams filled with reactive powder concrete *Technology* **9** 1177–87
- [41] Hassan R F, Al-Salim N H A and Jaber M H 2018 Effect of Polyvinyl Alcohol on flexural behavior of RC Bubble slabs under linear load *J. Eng. Appl. Sci.* **13** 3979–84
- [42] Ali I M, Nasr M S and Naje A S 2020 Enhancement of cured cement using environmental waste: particleboards incorporating nano slag *Open Eng.* **10** 273–81
- [43] Abed M, Nasr M and Hasan Z 2018 Effect of silica fume/binder ratio on compressive strength development of reactive powder concrete under two curing systems *MATEC Web of Conferences* vol 162 (EDP Sciences) p 02022
- [44] Nasr M S, Salih S A and Hassan M S 2016 Some Durability Characteristics of Micro Silica and Nano Silica Contained Concrete *J. Babylon Univ. Sci.* **24** 980–90
- [45] Nayel I H, Burhan S K and Nasr M S 2018 Characterisation of prepared rice husk ash and its effects on strength development in recycled aggregate concrete *IOP Conference Series: Materials Science and Engineering* vol 433 (IOP Publishing) p 12009
- [46] Shanbara H K, Shubbar A, Ruddock F and Atherton W 2020 Characterizing the Rutting Behaviour of Reinforced Cold Mix Asphalt with Natural and Synthetic Fibres Using Finite Element Analysis *Advances in Structural Engineering and Rehabilitation* (Springer) pp 221–7
- [47] Al Khafaji Z S and Ruddock F 2018 Study the retardant effect of using different sugar's types

- on setting time and temperature of cement paste *Int. J. Civ. Eng. Technol.* **9** 519–30
- [48] Shubbar A A F, Alwan H, Phur E Y, McLoughlin J and Al-khaykan A 2017 Studying the Structural Behaviour of RC Beams with Circular Openings of Different Sizes and Locations Using FE Method *Int. J. Civil, Environ. Struct. Constr. Archit. Eng.* **11** 849–52
- [49] Shubbar A A F, Atherton W, Jafer H M, Dulaimi A F and Al-Faluji D 2017 The Development of a New Cementitious Material Produced from Cement and GGBS *The 3rd BUiD Doctoral Research Conference-Faculty of engineering and IT (BUiD)* pp 51–63
- [50] Nasr M S, Hussain T H, Kubba H Z and Shubbar A A 2020 Influence of using high volume fraction of silica fume on mechanical and durability properties of cement mortar *J. Eng. Sci. Technol.* **15** 2492–506
- [51] Hussain T H, Nasr M S and Salman H J 2019 Effect of elevated temperature on degradation behavior of reactive powder concrete made with rubber tire wastes as an aggregate replacement *ARPN J. Eng. Appl. Sci.* **14** 775–80
- [52] Nasr M S, Salih S A and Hassan M S 2016 Pozzolanic Activity and Compressive Strength of Concrete Incorporated nano/micro Silica *Eng. Technol. J.* **34** 483–96
- [53] Hasan Z A, Abed M K and Nasr M S 2019 Studying the Mechanical Properties of Mortar Containing Different Waste Materials as a Partial Replacement for Aggregate *Int. Rev. Civ. Eng.* **10** 155–61
- [54] Al-Rifaie A, Al-Husainy A S and Shanbara H K 2020 Numerical study on the behaviour of end-plate beam-to-column connections under lateral impact loading *Int. J. Struct. Eng.* **10** 150–73
- [55] Nayel I H, Nasr M S and Abdulridha S Q 2020 Impact of elevated temperature on the mechanical properties of cement mortar reinforced with rope waste fibres *IOP Conference Series: Materials Science and Engineering* vol 671 (IOP Publishing) p 12080
- [56] Al-Khafaji Z S and Falah M W 2020 Applications of high density concrete in preventing the impact of radiation on human health *J Adv Res Dyn Control Syst* **12** 666–70
- [57] Shubbar A A, Al-Khafaji Z S, Nasr M S and Falah M W 2020 Using Non-Destructive Tests for Evaluating Flyover Footbridge: Case Study *Knowledge-Based Eng. Sci.* **1** 23–39
- [58] Abdulredha M, Abdulridha A, Shubbar A A, Alkhaddar R, Kot P and Jordan D 2020 Estimating municipal solid waste generation from service processions during the Ashura religious event *IOP Conference Series: Materials Science and Engineering* vol 671 (IOP Publishing) p 12075
- [59] Abdurraheem F S, Al-Khafaji Z S, Hashim K S, Muradov M, Kot P and Shubbar A A 2020 Natural filtration unit for removal of heavy metals from water *IOP Conference Series: Materials Science and Engineering* vol 888 (IOP Publishing) p 12034
- [60] Mohammed A-H, Hussein A H, Yeboah D, Al Khaddar R, Abdulhadi B, Shubbar A A and Hashim K S 2020 Electrochemical removal of nitrate from wastewater *IOP Conference Series: Materials Science and Engineering* vol 888 (IOP Publishing) p 12037
- [61] Alenezi A K, Hasan H A, Hashim K S, Amoako-Attah J, Gkantou M, Muradov M, Kot P and Abdulhadi B 2020 Zeolite-assisted electrocoagulation for remediation of phosphate from calcium-phosphate solution *IOP Conference Series: Materials Science and Engineering* vol 888 (IOP Publishing) p 12031
- [62] Al-Marri S, AlQuzweeni S S, Hashim K S, AlKhaddar R, Kot P, AlKizwini R S, Zubaidi S L and Al-Khafaji Z S 2020 Ultrasonic-Electrocoagulation method for nitrate removal from water *IOP Conference Series: Materials Science and Engineering* vol 888 (IOP Publishing) p 12073
- [63] Jabbar D N, Al-Rifaie A, Hussein A M, Shubbar A A, Nasr M S and Al-Khafaji Z S 2021 Shear behaviour of reinforced concrete beams with small web openings *Mater. Today Proc.* **34**