

Evaluation of Diamond Dressing Effect on Workpiece Surface Roughness by Way of Analysis of Variance

Frantisek HOLESOVSKY, Bingsuo PAN, Michael N. MORGAN, Andrej CZAN

Abstract: Wheel dressing is an important action in the grinding process. This paper reports on the comparative study of the performance of two types of diamond dresser tool measured in terms of ground surface roughness. For experiments were used two types of dressers, single point and multi-point diamond dresser. In addition to the dresser tool, the wheel dressing speed and dressing depth were taken into account as dressing variables. Cutting conditions were a constant; the results of dressing were observed for bearing steel 100Cr6. The experimental study was designed using an orthogonal array and experimental data were processed by the analysis-of-variance method (ANOVA). The results show that with a 95% confidence, dressing with a multi-point diamond tool results in a smoother ground surface than with a single point diamond tool. As expected, wheel dressing speed and dressing depth also have significant effects on surface roughness. However, wheel dressing speed is much more influential than dressing depth.

Keywords: ANOVA; diamond dresser; dressing; grinding; surface roughness

1 INTRODUCTION

In grinding, the grinding wheel has to be dressed periodically to restore wheel form and cutting efficiency [1, 7]. In diamond dressing, a number of parameters govern the process, including dressing depth, dressing lead/traverse rate, the type of dresser used and number of dressing passes [2, 3]. Owing to the significant effects of dressing conditions on the shape and distribution of abrasive grits, which directly affect grinding quality [4, 6, 8], grinding wheel wear, grinding force and grinding efficiency [9, 11, 13] the importance of proper dressing of grinding wheels on precision machining cannot be emphasized too strongly.

This article describes an investigation into the performance of a single point diamond dresser and of a

multi-point diamond dresser in cylindrical grinding of bearing steel [12]. Grinding wheel speed for dressing (v_s) and dressing depth (a_d) were also studied as independent variables. In grinding, which is commonly used as a finishing process, the quality of the generated surfaces is mainly evaluated by its roughness [4, 6, 10], thus the ground surface roughness was selected as the dependent variable. By means of analysis-of-variance (ANOVA) the performance of the two diamond dresser tools was compared with regard to ground surface roughness [5]. The percent contributions of grinding wheel speed and dressing depth to the total variation of surface roughness were evaluated in order to determine the significance of these two parameters for surface roughness.

Table 1 Design of dressing experiment and experimental data

| Test No. | v_s , m/s | a_d , mm | dresser | Ra , μm | Rz , μm | R_{max} , μm | Rt , μm |
|----------|-------------|------------|---------|----------------------|----------------------|----------------------------------|----------------------|
| 1 | 10 | 0.02 | SP | 0.849 | 5.38 | 6.75 | 6.88 |
| 2 | 10 | 0.04 | | 0.770 | 5.32 | 8.06 | 8.39 |
| 3 | 10 | 0.08 | | 0.929 | 6.14 | 7.99 | 8.37 |
| 4 | 20 | 0.02 | | 0.625 | 4.27 | 5.35 | 5.48 |
| 5 | 20 | 0.04 | | 0.562 | 4.02 | 4.79 | 5.20 |
| 6 | 20 | 0.08 | | 0.850 | 5.30 | 6.41 | 6.70 |
| 7 | 30 | 0.02 | | 0.385 | 2.98 | 3.59 | 3.76 |
| 8 | 30 | 0.04 | | 0.370 | 2.90 | 3.53 | 3.67 |
| 9 | 30 | 0.08 | | 0.538 | 3.93 | 4.70 | 4.85 |
| 10 | 10 | 0.02 | MP | 0.613 | 4.41 | 5.12 | 5.42 |
| 11 | 10 | 0.04 | | 0.676 | 4.64 | 5.59 | 6.00 |
| 12 | 10 | 0.08 | | 0.771 | 5.04 | 6.60 | 6.87 |
| 13 | 20 | 0.02 | | 0.354 | 2.64 | 3.16 | 3.28 |
| 14 | 20 | 0.04 | | 0.529 | 3.70 | 4.26 | 4.42 |
| 15 | 20 | 0.08 | | 0.589 | 4.13 | 5.06 | 5.29 |
| 16 | 30 | 0.02 | | 0.309 | 2.43 | 2.85 | 3.01 |
| 17 | 30 | 0.04 | | 0.326 | 2.56 | 2.96 | 3.12 |
| 18 | 30 | 0.08 | | 0.552 | 3.75 | 4.40 | 4.66 |

2 EXPERIMENTAL STUDY

Three dressing parameters, namely grinding wheel speed for dressing (v_s), dressing depth (a_d) and type of dresser were chosen as the variables. Grinding wheel speed was set at the three levels: 10 m/s, 20 m/s and 30 m/s;

dressing depth was set at the three levels: 0.02 mm, 0.04 mm and 0.08 mm. Two types of dressers were tested, single point diamond dresser (SP) and multi-point diamond dresser (MP). During dressing, the transverse rate of dresser was maintained at 1.0 mm/s and the dresser was cooled with cutting fluid at flow rate of approximately 10

l/min (cutting emulsion Robol 5% – produce company Triga). The design of experiment methodology is detailed in Tab. 1, together with the recorded data.

Tests listed in Tab. 1 were conducted in a random order. In every dressing test, the wheel was firstly dressed with a constant dressing depth of 0.08 mm for one pass, and then dressed with the set dressing depth to enable study of the subsequent pass. For each dressing test, four cylindrical surface grinding tests were undertaken successively. All grinding tests were completed on a cylindrical grinding machine (TOS BU 16). A SG grinding wheel ($\varnothing 300 \times 32$ mm), cutting fluid and a bearing steel workpiece ($\varnothing 85 \times 20.55$ mm) of hardness of 62 HRC were

employed. Grinding parameters were: grinding wheel speed = 30 m/s, workpiece speed = 20 m/min, in feed speed = 0.26 mm/min. To determine the resulting roughness, for every grinding test three measurements were taken at three different sections across the thickness of the workpiece with a Hommel Tester T1000 profilometer, produced by Hommelwerke GmbH. Hence each roughness value presented in Tab. 1 is the average of twelve measured roughness values. In each measurement, four surface parameters, R_a , R_z , R_{max} , R_t , were recorded. The scan distance was set at 4.8 mm and single sampling length at 0.8 mm, as shown in Fig. 1.

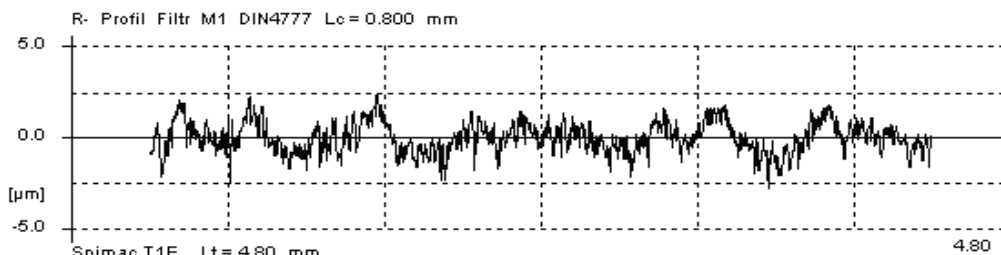


Figure 1 Profile of roughness (with single diamond dresser at $v_s = 20$ m/s, $a_d = 0.04$ mm)

3 EXPERIMENTAL RESULTS

The experimental data in Tab. 1 were processed to obtain the relationship between ground surface roughness and dressing parameters. This relationship is presented graphically in Figs. 2, 3 and 4.

Fig. 2 compares the effect of single point diamond

dressing on surface roughness with that of multi-point diamond dressing. In terms of all four measured surface parameters, the multi-point diamond dressing decreased their values by approximately 20% respectively, with those obtained in single point diamond dressing as a baseline. It indicates that multi-point diamond dressing can result in a smoother surface than single point diamond dressing.


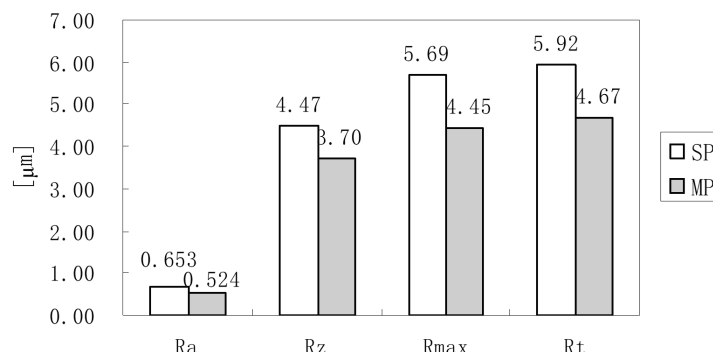


Figure 2 Comparison of effect of single point dressing on roughness with multi-point dressing

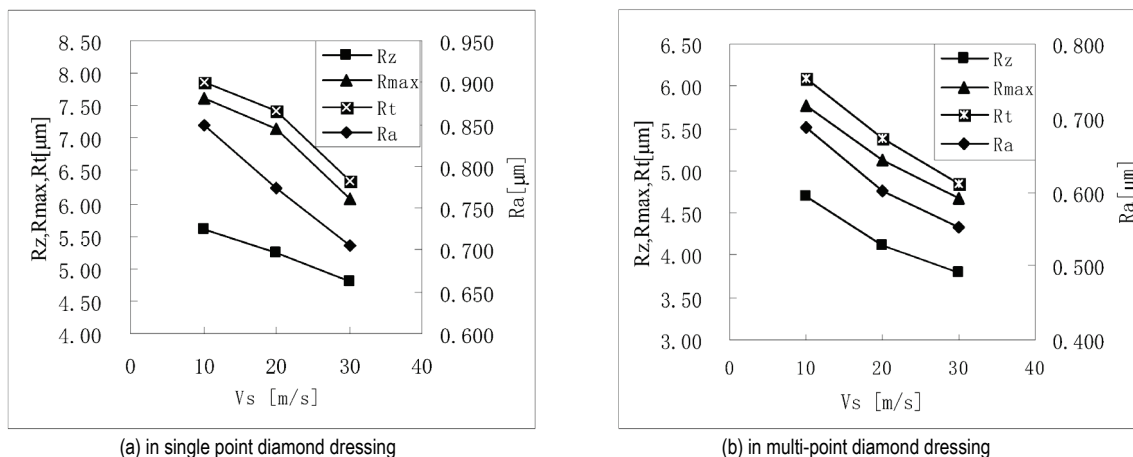

(a) in single point diamond dressing

(b) in multi-point diamond dressing

Figure 3 Effect of wheel speed on surface roughness ($A_d = 0.04$ mm)

4 STATISTICAL ANALYSIS OF RESULTS

4.1 Effect of Dresser Type

The effect of diamond dresser type was evaluated by Multivariate Analysis of Variance (MANOVA), for which data is shown in Tab. 2 and Tab. 3. This analysis was used to test the equality of the mean roughness values resulting from single point diamond dressing to those resulting from multi-point diamond dressing. In the MANOVA table, the F-test p-values for dresser, which are rather small, provide significant evidence that the average ground surface roughness for one type of dressing is different to the other when alpha is 0.05. Given their averages ($Ra = 0.524 \mu\text{m}$, $Rt = 4.67 \mu\text{m}$ for multi-point dresser and $Ra = 0.653 \mu\text{m}$, $Rt = 5.92 \mu\text{m}$ for single point dresser). A further conclusion can be drawn with 95% confidence level that by using a multi-point diamond dresser smoother surface can be produced. The MANOVA results for Rz and R_{max} were similar to those of Rt .

The p-values for the interaction terms, dresser* v_s and dresser* a_d , indicate that the strength of the effect of dresser type is dependent also on grinding wheel speed and dressing depth. To get an objective view of the impact of the dressing, it will affect the speed of the disc and the depth of dressing observed on two different types of dresser. However, the interaction between grinding wheel speed and dressing depth cannot be confirmed, owing to the large p-values.

Multivariate analysis of experimental data variance obtained in single point diamond dressing was shown in Tab. 4. According to the F-test p-values, it can be determined that both v_s and a_d are statistically significant


for Ra at confidence level alpha = 0.05. Based on variance components estimates, 76.67% of the total variation in Ra was due to the differences between v_s levels, while 18.82% resulted from the differences between a_d levels. For Rt , v_s is still a more significant factor, contributing a dominating percent, 83.40%, to its variation. It is reasonable to conclude that in single point diamond dressing and for the conditions studied, grinding wheel speed has a much stronger influence on Ra than dressing depth and Rt is strongly influenced by grinding wheel speed.

Table 2 MANOVA table for Ra versus type of dresser, v_s and a_d


| Source | DF | SS | MS | F Ratio | P |
|----------------|----|---------|---------|---------|-------|
| dresser | 1 | 0.07463 | 0.07463 | 27.07 | 0.006 |
| v_s | 2 | 0.37750 | 0.18875 | 68.47 | 0.001 |
| a_d | 2 | 0.12214 | 0.06107 | 22.15 | 0.007 |
| dresser* v_s | 2 | 0.02014 | 0.01007 | 3.65 | 0.125 |
| dresser* a_d | 2 | 0.01423 | 0.00712 | 2.58 | 0.191 |
| V_s*a_d | 4 | 0.00765 | 0.00191 | 0.69 | 0.634 |
| Error | 4 | 0.01103 | 0.00276 | | |
| Total | 17 | 0.62732 | | | |

Table 3 MANOVA table for Rt versus type of dresser, v_s and a_d

| Source | DF | SS | MS | F Ratio | P |
|----------------|----|---------|---------|---------|-------|
| dresser | 1 | 7.0063 | 7.0063 | 38.92 | 0.003 |
| v_s | 2 | 30.1457 | 15.0729 | 83.73 | 0.001 |
| a_d | 2 | 6.8607 | 3.4304 | 19.06 | 0.009 |
| dresser* v_s | 2 | 1.3462 | 0.6731 | 3.74 | 0.121 |
| dresser* a_d | 2 | 0.1431 | 0.0716 | 0.40 | 0.696 |
| V_s*a_d | 4 | 0.7110 | 0.1777 | 0.99 | 0.505 |
| Error | 4 | 0.7201 | 0.1800 | | |
| Total | 17 | 46.9331 | | | |

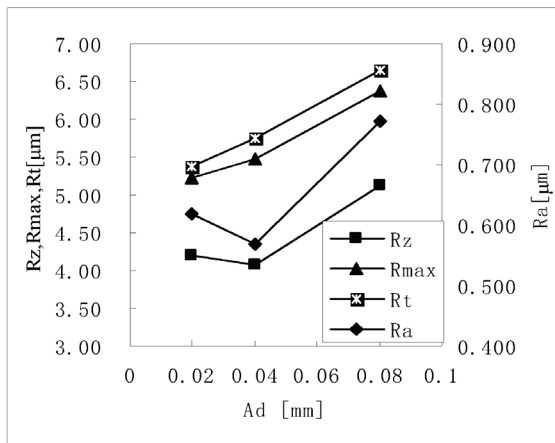

(a) in single point diamond dressing

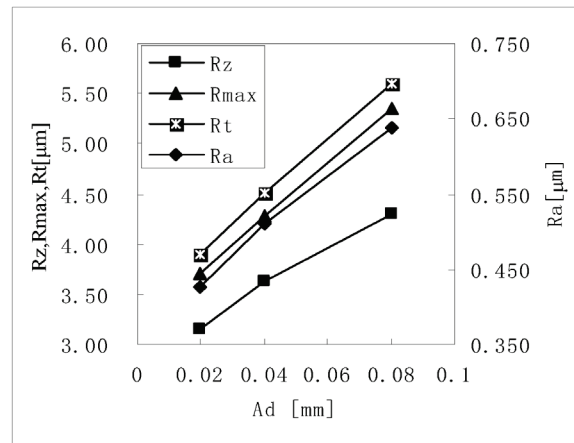

(b) in multi-point diamond dressing

Figure 4 Effect of dressing depth on surface roughness ($v_s = 30 \text{ m/s}$)

Tab. 5 is the ANOVA data for Ra and Rt obtained for multi-point diamond dressing. As the p-values for v_s are rather small, there is significant evidence for v_s main effects on Ra and Rt at alpha = 0.05 level. It contributed 59.90% and 66.27% to the total variation of Ra and of Rt , respectively. Likewise, the tests also indicate that factor a_d has a significant effect on surface roughness, by contributing 29.71% to the total variation of Ra and 29.28% to the variation of Rt . Hence a_d was approximately

half as influential as v_s . Compared to its effect in single diamond dressing, there is evident improvement. Therefore, in multi-point diamond dressing, considerable attention should be paid to the choice of dressing depth while strictly controlling grinding wheel speed in order to obtain a desirable dressing result.

The variation in Error values imply that the experimental conditions were well controlled and the experimental data are reliable.

Table 4 ANOVA result for single point diamond dressing

| Ra versus v_s, a_d | | | | | | |
|----------------------|----|----------|----------|---------|-------|-------------------|
| Source | DF | SS | MS | F Ratio | P | pct. contribution |
| v_s | 2 | 0.265520 | 0.132760 | 68.95 | 0.001 | 76.67% |
| a_d | 2 | 0.068071 | 0.034035 | 17.68 | 0.010 | 18.82% |
| Error | 4 | 0.007702 | 0.001925 | | | 4.51% |
| Total | 8 | 0.341293 | | | | 100% |

| Rt versus v_s, a_d | | | | | | |
|----------------------|----|---------|---------|---------|-------|-------------------|
| Source | DF | SS | MS | F Ratio | P | pct. contribution |
| v_s | 2 | 21.5830 | 10.7915 | 39.23 | 0.002 | 83.40% |
| a_d | 2 | 2.5350 | 1.2675 | 4.61 | 0.092 | 7.87% |
| Error | 4 | 1.1003 | 0.2751 | | | 8.73% |
| Total | 8 | 25.2184 | | | | 100% |

Table 5 ANOVA result for multi-point diamond dressing

| Ra versus v_s, a_d | | | | | | |
|----------------------|----|----------|----------|---------|-------|-------------------|
| Source | DF | SS | MS | F Ratio | P | pct. contribution |
| v_s | 2 | 0.132122 | 0.066061 | 24.07 | 0.006 | 59.90% |
| a_d | 2 | 0.068298 | 0.034149 | 12.44 | 0.019 | 29.71% |
| Error | 4 | 0.010976 | 0.002744 | | | 10.39% |
| Total | 8 | 0.211396 | | | | 100% |

| Rt versus v_s, a_d | | | | | | |
|----------------------|----|---------|---------|---------|-------|-------------------|
| Source | DF | SS | MS | F Ratio | P | pct. contribution |
| v_s | 2 | 9.9089 | 4.95444 | 59.92 | 0.001 | 66.27% |
| a_d | 2 | 4.4688 | 2.23441 | 27.03 | 0.005 | 29.28% |
| Error | 4 | 0.3307 | 0.08268 | | | 4.45% |
| Total | 8 | 14.7084 | | | | 100% |

5 APPLICATION IN PRODUCTION

The results were applied in optimizing the grinding of pin from steel 100Cr6. To achieve a good surface the multilevel feed of grinding wheel was used (Fig. 5). Feedrate was changed from 6.7 mm/min to 1.5 mm/min in the last step. Due to the use of abrasive grain Cubitron II the dressing speed was not changed, but three sizes of dressing speed were used in verifying test. For the dressing was used multi-point dresser. The peripheral speed of the grinding wheel was constant for all measuring – 45 m/s. During the optimization also the time of grinding was taken into account - time which was based on the initial state at the grinding, when the surface roughness $Ra = 0.39 \mu\text{m}$ was achieved.

Fig. 6 shows a high dependence of the surface quality on the longitudinal velocity of dresser, can simultaneously evaluate the effect of single degrees of feed rate of the tool in the working phase. It seems the dressing speed 50 mm/min is the most appropriate at the gradually decreasing feed speed from the value 6.6 to 2.5 mm/min (cycle A) - (Fig. 7). With this procedure, we achieve the repeated roughness Ra under $0.18 \mu\text{m}$ on CNC grinding machine. Under graph, we can then track the individual average values of surface roughness Ra and Rz .

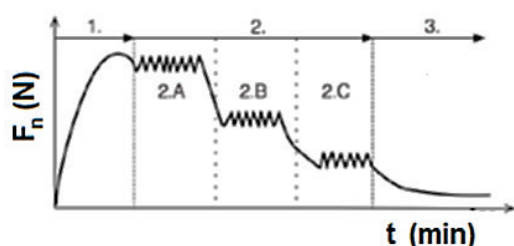


Figure 5 Grinding cycle, 2A - roughing, 2B - cleaning, 2C - finishing

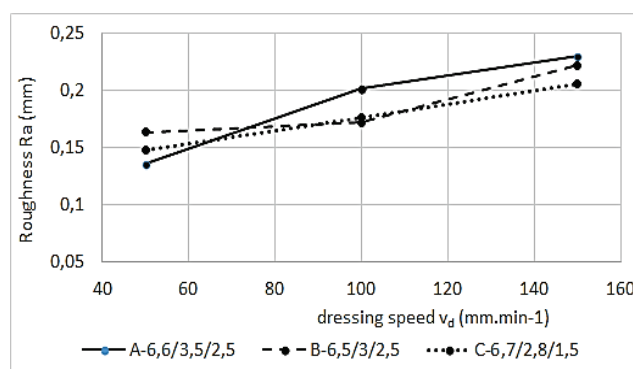


Figure 6 Dependence of surface roughness on the longitudinal velocity of dresser with various types of grinding cycle

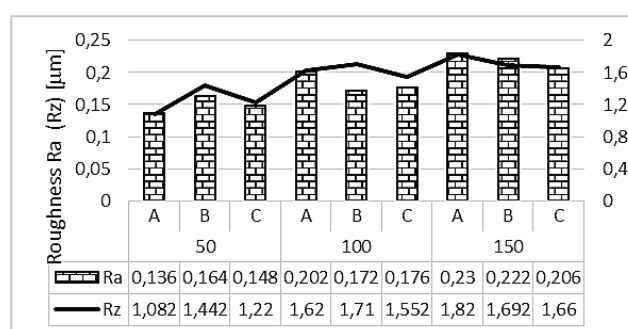


Figure 7 The dependence of the parameters of surface roughness and its numerical values on the type of cycle and the dressing speed

In said application at the using grinding wheel with grains of Cubitron II, this dependence is in force:

$$Ra = 0,022 \cdot v_d^{0,47}, \mu\text{m} \quad (1)$$

6 CONCLUSION

The conclusions drawn from this study are:

- 1) multi-point diamond dressing can result in a smoother

ground surface than single point diamond dressing; to a certain degree, the effect of dresser type depends also on grinding wheel speed and dressing depth;

- 2) in single point diamond dressing, grinding wheel speed for dressing has a dominant effect on surface roughness in terms of Ra and Rt , while dressing depth has only limited effect on Ra and no significant effect on Rt ;
- 3) in multi-point diamond dressing, both grinding wheel speed for dressing and dressing depth are statistically significant to surface roughness. However, grinding wheel speed is twice as effective as dressing depth;
- 4) the value of surface roughness can be determined using the mathematical relations:

for single point dresser – $Ra = 1,32 \cdot v_s^{-0,18}$, μm (2)

for multi-point dresser – $Ra = 1,12 \cdot v_s^{-0,21}$, μm (3)

the applicability of the relations has been verified by many experiments.

These values may provide the basis for further studies with differing abrasive and work material types.

Acknowledgements

This research was supported by the national grant GA CR 101/06/0508 – entitled "Research of surface properties with regard to possible impacts on the functionality of machine parts".

6 REFERENCES

- [1] Chen, X. & Rowe, W. B. (1996). Analysis and simulation of the grinding process. Part I: Generation of the grinding wheel surface. *Int. J. Math. Tools Manuf.*, 36(8), 871-882. [https://doi.org/10.1016/0890-6955\(96\)00116-2](https://doi.org/10.1016/0890-6955(96)00116-2)
- [2] Xue, L., Naghdy, F., & Cook, C. (2002). Monitoring of wheel dressing operations for precision grinding. *IEEE International Conference on Industrial Technology*, 2, 1296-1299.
- [3] Bianchi, E. C., Vargas, V. L., Magagnin, T. C. et al. (2003). Transverse cylindrical grinding of a eutectic alloy. *J. Braz. Soc. Mech. Sci. & Eng.*, 25(1), 79-84. <https://doi.org/10.1590/S1678-58782003000100011>
- [4] Fredj, B., Amamou, N., & Rezgui, R. (2002). Ground surface roughness prediction based upon experimental design and neural network models. *IEEE International Conference on Systems, Man and Cybernetics*, Tunisia: IEEE, 752-756. <https://doi.org/10.1109/ICSMC.2002.1176341>
- [5] Jurkovic, Z., Cukor, G., & Andrejcek, I. (2010). Improving the surface roughness at longitudinal turning using the different optimization methods. *Technical Gazette*, 17(4), 397-402.
- [6] Mochida, Y., Nishioka, T., Kubo, A., & Tamaki, J. (2010). Evaluation of diamond dressers and estimation of grinding performance by dressing force measurement. *Int. J. of Abrasive Technology*, 3(1), 37-50. <https://doi.org/10.1504/IJAT.2010.032461>
- [7] Transchel, R., Dold, C., Rabiey, M., & Wegener, K. (2012). Relevance of laser touch-dressed diamond tools for the dressing performance of vitrified-bonded silicon carbide wheels. *Int. J. of Abrasive Technology*, 5(1), 48-61. <https://doi.org/10.1504/IJAT.2012.046828>
- [8] Kuen-Ren, Ch. & Hong-Tsu, Y. (2010). Modelling on dressing effects in chemical mechanical polishing with diamond dressers. *Int. J. of Abrasive Technology*, 3(1), 1-10. <https://doi.org/10.1504/IJAT.2010.032458>
- [9] Malkin, S. (1989). *Grinding Technology – Theory and applications of machining with abrasives*. SME, Dearborn, Michigan.
- [10] Marinescu, D. I., Rowe, W. B., Dimitrov, B., & Inasaki, I. (2004). *Tribology of abrasive machining processes*. William Andrew, Inc. United States. <https://doi.org/10.1115/1.1819313>
- [11] Marinescu, D. I., Hitchiner, M. et al. (2007) *Handbook of Machining with Grinding Wheels*. CRC Press, Taylor & Francis Group, New York.
- [12] Bilek, O., Hrdina, J., Lukovics, I., Pero, R., & Samek, D. (2014). Improved shape of rotating grinding wheels for high speed grinding. *Technical Gazette*, 21(1), 63-68.
- [13] Morgan, N. M. & Jenkinson, D. I. (2006) *Advances in Manufacturing Technology – XX*. Proceeding of John Moores University, Liverpool.

Contact information:

Frantisek HOLESOVSKY, Prof.
Faculty of Technology and Production Management,
University of J. E. Purkyně,
Pasteurova 1, 400 96 Ústí nad Labem, Czech Republic
E-mail: holesovsky@fvtn.ujez.cz

Bingsuo PAN, PhD
Department of Exploration Engineering,
China University of Geosciences,
No. 388 Lumo Road, 430074 Wuhan, P. R. China
E-mail: tungsten76@hotmail.com

Michael N. MORGAN, Prof.
Advanced Manufacturing Technology Research Laboratory,
Liverpool John Moores University,
3 Byrom St, Liverpool L3 3AF, UK
E-mail: M.N.Morgan@ljmu.ac.uk

Andrej CZAN, Prof.
Department of Machining and Manufacturing Technology,
Faculty of Mechanical Engineering, University Žilina,
Univerzitná 8215/1, 010 26 Žilina, Slovak Republic
E-mail: andrej.czan@fstroj.uniza.sk